

An **IPRF** Research Report

Innovative Pavement Research Foundation

Airport Concrete Pavement Technology Program

CALIFORNIA

Highway Materials—Concrete Airfield Pavement

IPRF Project 01-G-002-05-3

REVIEW OF STATE HIGHWAY MATERIALS FOR CONCRETE AIRFIELD PAVEMENT CONSTRUCTION

**Programs Management Office
5420 Old Orchard Road
Skokie, IL 60077**

August 2010

An **IPRF** Research Report
Innovative Pavement Research Foundation
Airport Concrete Pavement Technology Program

CALIFORNIA

Highway Materials—Concrete Airfield Pavement

IPRF Project 01-G-002-05-3

REVIEW OF STATE HIGHWAY MATERIALS FOR CONCRETE AIRFIELD PAVEMENT CONSTRUCTION

Principal Investigator

Thomas J. Van Dam, P.E., Ph.D.

Contributing Authors

James M. Krstulovich
Linda M. Pierce, P.E., Ph.D.
Kurt D. Smith, P.E.
David G. Peshkin, P.E.

Applied Pavement Technology, Inc.
115 W. Main Street, Suite 400
Urbana, IL 61801
(217) 398-3977

Programs Management Office
5420 Old Orchard Road
Skokie, IL 60077

August 2010

This state portfolio has been prepared by the research team under IPRF project 01-G-002-05-3. The purpose of this document is to provide engineers with a “tool” for initial determination of the suitability of state specified materials for concrete pavement airport construction funded under the Airport Improvement Program (AIP) or Passenger Facility Charge (PFC) Program. It is emphasized that this document only considers the materials aspects of the specifications, and that the means and methods as specified under FAA AC 150/5370-10C must be followed. Additionally, the engineer must independently confirm the suitability of the state-specified material, and verify that neither the state nor the FAA specification has been subsequently modified since the time of this review.

The contents of this report reflect the views of the authors who are responsible for the facts and the accuracy of the data presented within. The contents do not necessarily reflect the official views and policies of the Federal Aviation Administration. This report does not constitute a standard, specification, or regulation.

TABLE OF CONTENTS

1. INTRODUCTION	1
CLASSIFICATION GROUPS.....	1
Group 1	2
Group 2	2
Group 3	4
Group 4	7
ASTM VERSUS AASHTO STANDARDS.....	7
2. SUMMARY AND COMPARISON OF SHA MATERIALS	10

LIST OF TABLES

Table 1. Example of SHA material standard meeting Group 1.....	2
Table 2. Example of SHA material standard meeting Group 2.....	3
Table 3. Example of SHA material standard meeting Group 3.....	4
Table 3. Example of SHA material standard meeting Group 3 (continued).....	5
Table 4. FAA and Idaho DOT coarse aggregate gradation requirements.....	6
Table 5. FAA and Idaho DOT aggregate gradation requirements.....	6
Table 6. Example of SHA material standard meeting Group 4.....	8
Table 7. “Equivalent” ASTM and AASHTO designations for test procedures or methods.	9
Table 8. Summary of applicable California state specifications to FAA items.....	11
Item P-154, Subbase Course.....	12
Item P-155, Lime-Treated Subgrade.....	15
Item P-208, Aggregate Base Course	16
Item P-209, Crushed Aggregate Base Course.....	21
Item P-219, Recycled Concrete Aggregate Base Course	26
Item P-304, Cement-Treated Base Course.....	29
Item P-306, Econocrete Base Course (Lean Mix Concrete Base Course).....	32
Item P-501, Portland Cement Concrete Pavement.....	35

LIST OF FIGURES

Figure 1. Gradation plot comparing FAA Item P-209 to ADOT Base, Class 1.....	9
--	---

1. INTRODUCTION

In several of its advisory circulars (AC), the Federal Aviation Administration (FAA) cites the allowable use of state highway agency (SHA) materials for certain airfield pavements subjected to specific traffic types. Maximizing the use of acceptable SHA materials on FAA projects can result in significant cost savings. This review of the California DOT materials specifications, conducted under IPRF Project 01-G-002-05-3, *Highway Materials – Concrete Airfield Pavements*, has been completed to provide guidance to engineers and contractors on what materials might be acceptable for the construction of concrete airfield pavements, and where they can be applied. It is noted that not all SHA-specified materials correspond to the FAA items under consideration. Specific FAA items considered in this review include:

- Item P-154 – Subbase Course
- Item P-155 – Lime-Treated Subgrade
- Item P-157 – Cement Kiln Dust (CKD) Treated Subgrade
- Item P-158 – Fly Ash Treated Subgrade
- Item P-208 – Aggregate Subbase
- Item P-209 – Crushed Aggregate Subbase
- Item P-211 – Lime Rock Base Course
- Item P-213 – Sand-Clay Base Course
- Item P-219 – Recycled Concrete Aggregate Base Course
- Item P-301 – Soil-Cement Base Course
- Item P-304 – Cement-Treated Base Course
- Item P-306 – Econocrete Base Course (Lean Mix Concrete Base Course)
- Item P-401/403 – Plant Mix Bituminous Pavements
- Item P-501 – Portland Cement Concrete Pavement

This document provides engineers with a “tool” for initial determination of the suitability of state specified materials for airport construction funded under the Airport Improvement Program (AIP) or Passenger Facility Charge (PFC) Program. It is emphasized that this document only considers the materials aspects of the specifications, and that the means and methods as specified under FAA AC 150/5370-10C must be followed. Additionally, the engineer using this document must independently confirm the suitability of the SHA-specified material, and verify that neither the state nor the FAA specification has been subsequently modified since the time of this review.

Classification Groups

In this document, the material standards and special provisions for each SHA were classified into four categories based on how well they met the prevailing FAA item. The four categories are:

- Group 1 – The material meets or exceeds the requirement of the respective FAA standard and differs only by the common designation and should be acceptable for use.
- Group 2 – The material does not meet the FAA standard, but should be acceptable for use on airfields supporting aircraft less than 60,000 lbs maximum takeoff weight.
- Group 3 – The material does not meet the FAA standard, but might be used subject to specific considerations (improvement to controlling material characteristic).
- Group 4 – The material does not meet the FAA standard.

The following describes the process by which each SHA material standard and special provision was categorized into the four groups.

Group 1

As described above, Group 1 includes SHA material standards and special provisions that meet or exceed the test methods and material requirements of the equivalent FAA item and thus may be considered for use on FAA projects with no modifications or revisions. For example, a comparison of California DOT Section 24, *Lime Stabilization* with FAA Item P-155, *Lime-Treated Subgrade* is shown in table 1. In this comparison, the FAA Item P-155 requires that the lime be in accordance with ASTM C977, *Standard Specification for Lime for Soil Stabilization*. This is the same requirement as specified for the California lime stabilized material. All other FAA requirements are also met in the California DOT specification, therefore, these two specifications are considered equivalent and the California specified material was assigned a Group 1 categorization and may be considered as equivalent to FAA Item P-155.

Table 1. Example of SHA material standard meeting Group 1.

Item	LIME-TREATED SUBGRADE																	
	California DOT	FAA																
Agency Specification	Section 24, Lime Stabilization	Item P-155, Lime-Treated Subgrade																
Description	This work shall consist of mixing lime and water with soil and compacting the mixture.	One or more courses of a mixture of soil, lime, and water.																
Test Methods Referenced	<ul style="list-style-type: none"> ASTM C977 	<ul style="list-style-type: none"> ASTM C977 																
Materials	<ul style="list-style-type: none"> Soil Lime Water 	<ul style="list-style-type: none"> Lime Water 																
Relevant Material Requirement(s)	<p>Lime: Lime shall conform to the requirements in ASTM C977, except that when a 250-gram test sample of quicklime is dry sieved in a mechanical sieve shaker for 10 minutes ± 30 seconds, it shall conform to the following grading requirements:</p> <table border="1"> <thead> <tr> <th>Sieve</th> <th>% Passing</th> </tr> </thead> <tbody> <tr> <td>3/8 in.</td> <td>98 – 100</td> </tr> <tr> <td>#100</td> <td>0 – 25</td> </tr> <tr> <td>#200</td> <td>0 – 14</td> </tr> </tbody> </table>	Sieve	% Passing	3/8 in.	98 – 100	#100	0 – 25	#200	0 – 14	<p>Lime:</p> <ul style="list-style-type: none"> Hydrated lime meeting ASTM C977 Commercial lime slurry consisting of hydrated lime meeting the following: <ul style="list-style-type: none"> Grade 1 “dry solids content” $\geq 31\%$ Grade 2 “dry solids content” $\geq 35\%$ Chemical composition, $\geq 70\%$ CaO and MgO <table border="1"> <thead> <tr> <th>Sieve</th> <th>Residue, % Retained</th> </tr> </thead> <tbody> <tr> <td>#6</td> <td>0.0</td> </tr> <tr> <td>#10</td> <td>≤ 1.0</td> </tr> <tr> <td>#30</td> <td>$\leq 2\text{--}5$</td> </tr> </tbody> </table> 	Sieve	Residue, % Retained	#6	0.0	#10	≤ 1.0	#30	$\leq 2\text{--}5$
Sieve	% Passing																	
3/8 in.	98 – 100																	
#100	0 – 25																	
#200	0 – 14																	
Sieve	Residue, % Retained																	
#6	0.0																	
#10	≤ 1.0																	
#30	$\leq 2\text{--}5$																	

Group 2

SHA material standards and special provisions categorized as Group 2 include materials that do not meet the FAA standard but could be used on concrete airfield pavements supporting aircraft less than 60,000 lbs maximum takeoff weight. An example of a SHA material meeting a Group 2 classification is shown in table 2. In this table, the Alabama DOT Section 301, *Soil, Soil Aggregate, and Aggregate, Base and Subbases* is compared to FAA Item P-154, *Subbase Course*. FAA Item P-154 requires that the subbase material meet ASTM D4318, *Standard Method of Test for Determining the Liquid Limit, Plastic Limit, and Plasticity Index of Soils*, while the Alabama specification requires the material to meet AASHTO T 89 and T 90, *Standard*

Method of Test for Determining the Liquid Limit of Soils and Standard Method of Test for Determining the Plastic Limit and Plasticity Index of Soils, respectively. The two specifications differ in aggregate gradation requirements; however, this difference was not deemed to be significant regarding performance for pavements carrying aircraft weighing 60,000 lbs or less since the SHA-specified material is used for pavements constructed to withstand 80,000-lb truck loads. Therefore in this case, the Alabama DOT Section 301, *Soil, Soil Aggregate, and Aggregate, Base and Subbases* might be considered as a suitable replacement for FAA Item P-154, *Subbase Course* for pavements serving aircraft weighing less than 60,000 lbs.

Table 2. Example of SHA material standard meeting Group 2.

Item	SUBBASE COURSE											
	Alabama DOT	FAA										
Agency Specification	Section 301, Soil, Soil Aggregate, and Aggregate, Base and Subbases	Item P-154, Subbase Course										
Description	Base and subbase materials consist of natural soil, natural soil and natural aggregate combinations, manufactured aggregates, or any combination of these with or without a stabilizing agent.	Subbase course composed of granular materials constructed on prepared subgrade or underlying course.										
Test Methods Referenced	<ul style="list-style-type: none"> ▪ AASHTO T 89 ▪ AASHTO T 90 	<ul style="list-style-type: none"> ▪ ASTM D4318 										
Materials	<ul style="list-style-type: none"> ▪ Soil ▪ Soil aggregate ▪ Aggregate 	<ul style="list-style-type: none"> ▪ Aggregate 										
Relevant Material Requirement(s)	<p>Granular soil material:</p> <ul style="list-style-type: none"> ▪ Granular soil material shall be of the kind and general character of sand-clay, topsoil, sand, soft sand rock, and so on, or a combination of these. ▪ Quality requirements: <ul style="list-style-type: none"> – Clay content, range <ul style="list-style-type: none"> ◦ Type A, 2 – 18% ◦ Type B, 1 – 18% ◦ Type C, 1 – 16% – Liquid Limit \leq 25 – Plasticity Index \leq 6 	<p>Subbase material:</p> <ul style="list-style-type: none"> ▪ Subbase material shall consist of hard durable particles or fragments of granular aggregates blended with fine sand, clay, stone dust, or other similar binding or filler materials. ▪ Quality requirements: <ul style="list-style-type: none"> – Free from vegetable matter, lumps or excessive amounts of clay, and other objectionable or foreign substances. ▪ Material passing the #40: <ul style="list-style-type: none"> – Liquid Limit \leq 25 – Plasticity Index \leq 6 ▪ Material finer than 0.02 mm shall be < 3%. 										
Relevant Material Requirement(s)	<p>Soil aggregate material:</p> <ul style="list-style-type: none"> ▪ Soil aggregate material shall be of various types, such as clay gravel, clay gravel-sand, float gravel, soft sand rock, and so on. ▪ Quality requirements: <ul style="list-style-type: none"> – Clay content, range <ul style="list-style-type: none"> ◦ Type A, 2 – 15% ◦ Type B, 1 – 14% ◦ Type C, 1 – 12% – Liquid Limit \leq 26 – Plasticity Index \leq 6 	<ul style="list-style-type: none"> ▪ Gradation Requirements: <table border="1" data-bbox="1052 1594 1313 1742"> <thead> <tr> <th>Sieve</th> <th>% Passing</th> </tr> </thead> <tbody> <tr> <td>3-in.</td> <td>100</td> </tr> <tr> <td>#10</td> <td>20 – 100</td> </tr> <tr> <td>#40</td> <td>5 – 60</td> </tr> <tr> <td>#200</td> <td>0 – 8</td> </tr> </tbody> </table>	Sieve	% Passing	3-in.	100	#10	20 – 100	#40	5 – 60	#200	0 – 8
Sieve	% Passing											
3-in.	100											
#10	20 – 100											
#40	5 – 60											
#200	0 – 8											

Group 3

Group 3 materials include SHA-specified materials that, with some modification, would meet the salient material specifications as identified in the relevant FAA items. SHA material specifications that were identified as meeting Group 3 included all of the salient material characteristics of the analogous FAA item, but differed slightly in material specifications (i.e., aggregate gradation, liquid limit, or plasticity index), or excluded several of the material characteristics that conceivably could be added to the SHA material specification to meet the FAA item requirements. The distinguishing feature of a Group 3 classification is that the SHA-specified material could meet the FAA item requirements with relatively little effort.

An example of a SHA material meeting a Group 3 classification is shown in table 3. In this table, FAA Item P-501, *Portland Cement Concrete Pavement* is compared to Idaho DOT Section 409, *Portland Cement Concrete Pavement*. As can be seen, the two specifications closely align, with the FAA Item P-501 requiring that the aggregate meet ASTM C131 (LA Wear), that the cement shall meet ASTM C150, C595, or C1157, and that the pozzolan material shall meet ASTM C618. In comparison, the Idaho specification requires that the aggregate shall meet AASHTO T 96 (*Standard Method of Testing for Resistance to Degradation of Small-Size Coarse Aggregate by Abrasion and Impact in the Los Angeles Machine*), AASHTO M 85 (*Standard Specification for Portland Cement*) or M 240 (*Standard Specification for Blended Hydraulic Cement*), which are equivalent to ASTM C150 (*Standard Specification for Portland Cement*) and C595 (*Standard Specification for Blended Hydraulic Cement*), respectively. The Idaho specification does not specify a requirement for pozzolanic materials. But as can be seen in tables 4 and 5, the gradations between the two specifications differ slightly, but not so much so that there is a range of gradations that would meet both specifications.

Table 3. Example of SHA material standard meeting Group 3.

Item	PORTLAND CEMENT CONCRETE PAVEMENT	
	Idaho DOT	FAA
Agency Specification	Section 409, Portland Cement Concrete Pavement	Item P-501, Portland Cement Concrete Pavement
Description	This work shall consist of constructing a pavement composed of portland cement concrete.	Pavement course composed of portland cement concrete, with or without reinforcement.
Test Methods Referenced	<ul style="list-style-type: none"> ▪ AASHTO M 6 ▪ AASHTO M 80 ▪ AASHTO M 85 or AASHTO M 240 ▪ AASHTO T 96 ▪ AASHTO T 176 ▪ AASHTO T 303 ▪ Idaho T-15 	<ul style="list-style-type: none"> ▪ ASTM C33 ▪ ASTM C131 ▪ ASTM C150, ASTM C595, or ASTM C1157 ▪ ASTM C618
Materials	<ul style="list-style-type: none"> ▪ Portland cement ▪ Water ▪ Aggregate ▪ Concrete admixtures ▪ Fly ash ▪ Concrete curing materials 	<ul style="list-style-type: none"> ▪ Fine and coarse aggregate ▪ Cement, fly ash, natural pozzolan, or ground blast furnace slag ▪ Water ▪ Cover material for curing ▪ Admixtures

Table 3. Example of SHA material standard meeting Group 3 (continued).

Item	PORTLAND CEMENT CONCRETE PAVEMENT	
	Idaho DOT	FAA
Relevant Material Requirement(s)	<p>Coarse aggregate:</p> <ul style="list-style-type: none"> ▪ Aggregates shall be reasonably free from wood, roots, bark, soft or disintegrated pieces, or other detrimental matter. ▪ Blend sand may be used to correct deficiencies in gradation. ▪ Quality requirements: <ul style="list-style-type: none"> – Wear, max loss: 35% – Degradation (Idaho T-15): <ul style="list-style-type: none"> ○ Percent passing the #200: <ul style="list-style-type: none"> ▪ Original: 5 – 8; ▪ Final \leq Original + 5 ▪ Original: 9; Final \leq 14 ▪ Original: 10; Final \leq 15 ○ Sand equivalent: <ul style="list-style-type: none"> ▪ Original: \geq 36; Final \geq 30 ▪ Original: 30 – 35; Final \geq 25 ▪ Deleterious content requirements, max content: <ul style="list-style-type: none"> – Clay lumps, 0.5% – Clay lumps/friable particles, 2.0% – Coal/lignite, 1.0% – Minus #200 material, 1.0% – Flat, elongated particles (5:1), 15% – Other, 5.0% <p>Fine aggregate:</p> <ul style="list-style-type: none"> ▪ Aggregates shall be reasonably free from wood, roots, bark, soft or disintegrated pieces, or other detrimental matter. ▪ Quality requirements: <ul style="list-style-type: none"> – Soundness meeting AASHTO M 6 – Sand equivalent \geq 70 ▪ Deleterious content requirements, max content: <ul style="list-style-type: none"> – Clay lumps, 1.0% – Coal/lignite, 1.0% – Other, 5.0% ▪ Degradation (Idaho T-15): <ul style="list-style-type: none"> – Percent passing the #200: <ul style="list-style-type: none"> ○ Original: 5 – 8; ○ Final \leq Original + 5 ○ Original: 9; Final \leq 14 ○ Original: 10; Final \leq 15 – Sand equivalent: <ul style="list-style-type: none"> ○ Original: \geq 36; Final \geq 30 ○ Original: 30 – 35; Final \geq 25 <p>Portland cement:</p> <ul style="list-style-type: none"> ▪ Type I, II, III, or V meeting ASTM C150 ▪ Type IS or IP meeting ASTM C595 ▪ Type GU, HE, HS, MH, or LH meeting ASTM C1157 	<p>Coarse aggregate:</p> <ul style="list-style-type: none"> ▪ Crushed or uncrushed gravel, crushed stone, air-cooled blast furnace slag, or crushed recycled PCC. ▪ Coarse aggregate shall meet ASTM C33. ▪ Quality requirements: <ul style="list-style-type: none"> – Wear (C131), max loss <ul style="list-style-type: none"> ○ Used as surface course, 40% ○ Used as base course, 50% <p>Fine aggregate:</p> <ul style="list-style-type: none"> ▪ Fine aggregate shall meet ASTM C33. <p>Portland cement:</p> <ul style="list-style-type: none"> ▪ Type I, II, III, or V meeting ASTM C150 ▪ Type IS or IP meeting ASTM C595 ▪ Type GU, HE, HS, MH, or LH meeting ASTM C1157

Table 4. FAA and Idaho DOT coarse aggregate gradation requirements.

Sieve	% Passing									
	FAA					ITD				
	2" max ¹	1" max	1-1/2" max ¹	3/4" max	1" max	2a	2b	3	4 ²	5 ²
2-1/2"	100	--	--	--	--	--	--	--	--	100
2"	90–100	--	100	--	--	--	--	--	100	95–100
1-1/2"	35–70	100	90–100	--	100	--	--	100	95–100	--
1"	0–15	95–100	20–55	100	95–100	100	100	95–100	--	35–70
3/4"	--	--	0–15	90–100	--	95–100	80–100	--	35–70	--
1/2"	0–5	25–60	--	--	25–60	--	--	25–60	--	10–30
3/8"	--	--	0–5	20–55	--	20–55	10–40	--	10–30	--
#4	--	0–10	--	0–10	0–10	0–10	0–4	0–10	0–5	0–5
#8	--	0–5	--	0–5	0–5	0–5	--	0–5	--	--

¹ Aggregate shall be furnished in two size groups when the nominal max size is greater than 1 in.² Sizes 4 and 5 shall be a combination of two or more coarse aggregate sizes.

Table 5. FAA and Idaho DOT aggregate gradation requirements.

Sieve	FINE AGGREGATE	
	% Passing	
	FAA	ITD
3/8 in	100	100
#4	95–100	95–100
#8	80–100	--
#16	50–85	45–80
#30	25–60	--
#50	10–30	10–30
#100	2–10	2–10
#200	--	0–2 ³

³ The percent passing may be ≤ 3 if the sand equivalent is ≥ 80 .

Thus, for this comparison the Idaho DOT Section 409 specification meets the FAA Item 501 specifications in all critical requirements except for aggregate gradation. Although the Idaho DOT aggregate specification is slightly different from the FAA Item P-501 gradation, the differences are such that the Idaho DOT gradation could meet the FAA Item P-501 gradation and thus modification is an option. A contractor may choose to modify the Idaho DOT-specified aggregate gradation to meet the FAA P-501 specification; therefore, the Idaho DOT specified material is characterized as a Group 3.

Alternatively, it is stated under FAA Item P-501:

The Engineer shall specify the aggregate to be furnished from the table shown in this note. The appropriate gradation shall be inserted into Table 2. Insert points are denoted by asterisks. Where locally available aggregates cannot be economically blended to meet the grading requirements, the gradations may be modified by the Engineer to fit the characteristics of such locally available aggregates.

This indicates the engineer can choose to accept the local gradation, in this case changing the category from a Group 3 to a Group 1. It is noted that he/she would still need to file a “modification to standard” request to the FAA to obtain material approval.

Similarly, the FAA Item P-501 also makes allowance for regional differences in aggregate percent wear requirements, as stated:

The Engineer shall specify the percentage of wear. It should not exceed 40 percent. In certain cases where aggregate of this quality cannot be obtained economically, aggregate with a higher percentage of wear may be used if a satisfactory service record of at least 5 years' duration under similar conditions of service and exposure has been demonstrated.

Again, this provides a mechanism for the engineer to accept aggregate with a higher percentage of wear, but with the stipulation that a “modification to standard” request would need to be filed with the FAA to obtain material approval.

Group 4

SHA material standards and special provisions that have been categorized as Group 4 have little to no semblance to the relevant FAA item or require significant modification that would more than likely render these materials as not cost effective. An example of a SHA material receiving a Group 4 classification is shown in table 6. This table compares FAA Item P-209, *Crushed Aggregate Base Course* to Arizona DOT Section 303, *Aggregate Subbases and Aggregate Bases*. In this case, the gradations for the FAA Item P-209 and Arizona DOT Aggregate Base, Class 1 differ in a non-reconcilable way as shown clearly in figure 1. Whereas other properties of the specification could be modified, it is impossible to modify the Arizona DOT Aggregate Base, Class 1 gradation to meet the FAA Item P-209 specification. Since the material specifications are irreconcilably different, the Arizona DOT material cannot meet the FAA requirements and therefore is characterized as Group 4. Note that the Arizona DOT Aggregate Base, Class 2 base was assigned to Group 2 and Group 3.

ASTM Versus AASHTO Standards

Table 7 shows the ASTM and comparable AASHTO test methods used in the evaluation of FAA items and SHA material specifications, respectively. It is noted that these “equivalent” specifications do not always match one another exactly. For example, a slight difference in gradation is observed for fine aggregate in ASTM C33 (0 to 10 percent passing the No. 100 sieve) versus AASHTO M 6 (2 to 10 percent passing the No. 100 sieve). In addition, there is often a lag time behind a change in one (e.g. ASTM) and when it is accepted, if ever, by the other (e.g. AASHTO). A recent example of this is the allowance for 5 percent interground limestone in portland cement. ASTM C150 adopted this in 2004 and yet it wasn’t until 2007 that limestone additions were allowed in AASHTO M 85. And although many states defer to AASHTO standards, most use some variation of the material specifications and test methods to create their own unique practice. And, in some cases, no equivalent AASHTO standard exists for an existing ASTM standard (e.g., no AASHTO equivalent exists for ASTM C1157, *Performance Specified Hydraulic Cement*).

Table 6. Example of SHA material standard meeting Group 4.

Item	CRUSHED AGGREGATE BASE COURSE	
	Arizona DOT	FAA
Agency Specification	Section 303, Aggregate Subbases and Aggregate Bases	Item P-209, Crushed Aggregate Base Course
Description	This work shall consist of furnishing, placing, and compacting aggregate subbases and aggregate bases.	Base course composed of crushed aggregate.
Test Methods Referenced	<ul style="list-style-type: none"> ▪ AASHTO T 90 ▪ AASHTO T 96 	<ul style="list-style-type: none"> ▪ ASTM C29 ▪ ASTM C88 ▪ ASTM C131 ▪ ASTM D2419 ▪ ASTM D4318
Materials	<ul style="list-style-type: none"> ▪ Aggregate Base Classes 1 and 2 	<ul style="list-style-type: none"> ▪ Crushed coarse aggregate ▪ Fine aggregate
Relevant Material Requirement(s)	<p>Aggregate:</p> <ul style="list-style-type: none"> ▪ Aggregate shall consist of stone or gravel free of vegetable matter and other deleterious substances. ▪ Quality requirements: <ul style="list-style-type: none"> ◦ Wear (AASHTO T 96), max loss: 40% ◦ Plasticity Index (AASHTO T 90): <ul style="list-style-type: none"> ▪ Classes 1 and 2 ≤ 3 ▪ For Class 1 through Class 3 aggregate, the amount of fractured coarse aggregate particles shall be at least 30 percent, when tested in accordance with the requirements of Arizona Test Method 212. 	<p>Coarse aggregate:</p> <ul style="list-style-type: none"> ▪ Crushed coarse aggregate shall be crushed stone, crushed air-cooled blast furnace slag, or crushed gravel. ▪ Crushed slag unit weight: $\geq 70 \text{ lb/ft}^3$ ▪ Crushed coarse aggregate shall have $\geq 90\%$ of the material having ≥ 2 fractured faces and 100% having ≥ 1. ▪ In frost areas, material finer than 0.02 mm shall be $< 3\%$. <p>Quality requirements:</p> <ul style="list-style-type: none"> – Wear (ASTM C131), max loss: 45% – Soundness (ASTM C88), max loss: 12% – Material passing the #40: <ul style="list-style-type: none"> ▪ Liquid Limit ≤ 25 ▪ Plasticity Index ≤ 4 <p>Fine aggregate requirements:</p> <ul style="list-style-type: none"> ▪ Fine aggregate shall be fines produced from the crushing operation. ▪ Sand equivalent value ≥ 35 (ASTM D2419)
Important Deviations		
Level of Acceptability for Use	<ul style="list-style-type: none"> ▪ Group 2 – Except for liquid limit, ASTM C88, percent fractured faces, and aggregate gradation, the state-specified Class 2 material meets all FAA material requirements. The state-specified material may be used on airfields supporting aircraft with less than 60,000 lbs maximum takeoff weight. ▪ Group 3 – The state-specified Class 2 material may be used on FAA facilities if the requirements for aggregate gradation, liquid limit, ASTM C88, and percent fractured faces are met. ▪ Group 4 – The state-specified Class 1 material is unable to meet FAA aggregate gradation requirements and therefore is not acceptable for use on FAA facilities. 	

In preparing this document of state practice, the research team considered these factors when comparing the SHA materials to relevant FAA items and assigning Groups. The engineer should use this document only as a tool for initial determination of material suitability and is still responsible for ensuring that the FAA standards are met.

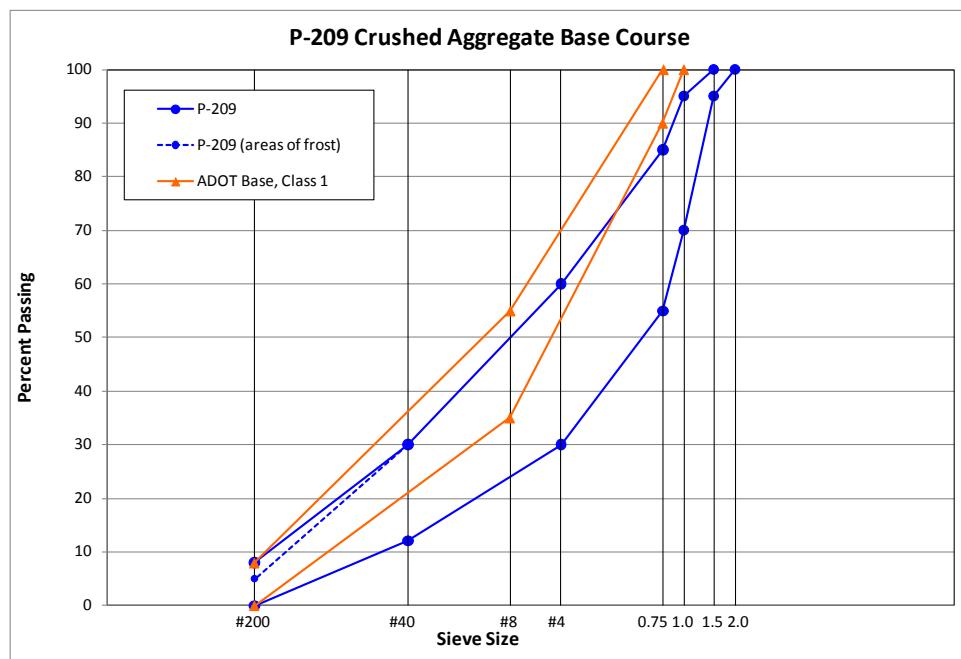


Figure 1. Gradation plot comparing FAA Item P-209 to ADOT Base, Class 1.

Table 7. “Equivalent” ASTM and AASHTO designations for test procedures or methods.

Test Procedure or Method	ASTM Test Method	AASHTO Test Method
Standard Test Method for Bulk Density (Unit Weight) and Voids in Aggregate	C29	T 19
Standard Specification for Concrete Aggregates	C33	M 6
Standard Test for Soundness of Aggregate by Use of Sodium Sulfate or Magnesium Sulfate	C88	T 104
Standard Test Method for Resistance to Degradation of Small-Size Coarse Aggregate by Abrasion and Impact in the Los Angeles Machine	C131	T 96
Standard Specification for Portland Cement	C150	M 85
Standard Specification for Blended Hydraulic Cement	C595	M 240
Standard Specification for Coal Fly Ash and Raw or Calcined Natural Pozzolan for Use in Concrete	C618	M 295
Standard Specification for Lime for Soil Stabilization	C977	M 216
Standard Specification for Ground Granulated Blast-Furnace Slag for Use in Concrete	C989	M 302
Standard Performance Specification for Hydraulic Cement	C1157	N/A
Standard Specification for Cutback Asphalt	D2028	M 81
Specification for Cationic Emulsified Asphalt	D2397	M 208
Test Method for Sand Equivalent Values of Soils and Fine Aggregate	D2419	T 176
Standard Test Methods for Liquid Limit, Plastic Limit, and Plasticity Index of Soils	D4318	T 89/T 90

2. SUMMARY AND COMPARISON OF SHA MATERIALS

The following summarizes and compares the California Department of Transportation (DOT) materials specifications and special provisions against the applicable FAA Items. Each of the state materials specifications have been categorized into at least one of the four previously defined acceptance groups (see table 8). Detailed tabular comparisons are presented in the remainder of this portfolio by FAA item; for each item, these tables provide the following information:

- Specification Designation and Title
- Description
- Test Methods Referenced
- Materials
- Relevant Material Requirements
- Important Deviations
- Level of Acceptability for Use
- Additional Specifications

Caltrans 2006 *Standard Specifications for Road and Bridge Construction* were used in this comparison and can be accessed at: http://www.dot.ca.gov/hq/esc/oe/specifications/std_specs/. The standard special provisions can be accessed at: <http://www.dot.ca.gov/hq/esc/oe/specifications/SSPs/>.

Table 8. Summary of applicable California state specifications to FAA items.

Specification	FAA ITEM Level of Acceptability for Use ⁽⁴⁻⁷⁾								
	<u>P-154</u>	<u>P-155</u>	<u>P-208</u>	<u>P-209</u>	<u>P-219</u>	<u>P-304</u>	<u>P-306</u>	<u>P-403⁸</u>	<u>P-501</u>
Section 24 – Lime Stabilization		1							
Section 25 – Subbase									
Class 1 – 3	2, 3								
Class 4 and 5	4								
Section 26, Aggregate Bases									
Class 2 and Class 3 SSP 06-080 1-1/2 in.			2, 3	2, 3	2, 3				
Class 3 SSP 06-080 3/4 in. and Class 3 SSP 06-100 3/4 in.			2, 3	4	2, 3				
Section 27, Cement Treated Bases						2, 3			
Section 28, Lean Concrete Base							2, 3		
Section 39, Asphalt Concrete ⁸								1	
Section 40, Portland Cement Concrete Pavement									2, 3

Notes:

⁴ Group 1 – The material meets or exceeds the requirement of the respective FAA standard and differs only by the common designation.

⁵ Group 2 – The material does not meet the FAA standard, but can be used on airfields supporting aircraft with less than 60,000 lbs maximum takeoff weight.

⁶ Group 3 – The material does not meet the FAA standard, but might be used subject to specific considerations (improvement to or modification of a controlling material characteristic).

⁷ Group 4 – The material does not meet the FAA standard.

⁸ According to AC 150/5379-10, SHA specifications for bituminous pavements may be used for P-403 as stabilized base under Item P-501, as well as for pavements not subjected to aircraft loading, such as access and perimeter roads, and for pavements designed for aircraft weights of 12,500 lbs or less.

Item	SUBBASE COURSE											
	Caltrans	FAA										
Agency Specification	Section 25, Aggregate Subbases	Item P-154, Subbase Course										
Description	This work shall consist of furnishing, spreading, and compacting aggregate subbases. Aggregate subbases are designated as Class 1, Class 2, Class 3, Class 4, or Class 5.	Subbase course composed of granular materials constructed on prepared subgrade or underlying course.										
Test Methods Referenced	<ul style="list-style-type: none"> ▪ California Test 217 ▪ California Test 301 	<ul style="list-style-type: none"> ▪ ASTM D 4318 										
Materials	<ul style="list-style-type: none"> ▪ Aggregate 	<ul style="list-style-type: none"> ▪ Aggregate 										
Relevant Material Requirement(s)	<p>Coarse aggregate:</p> <ul style="list-style-type: none"> ▪ Aggregate may include material processed from reclaimed asphalt concrete, portland cement concrete, lean concrete base, cement-treated base, or a combination of these. <ul style="list-style-type: none"> – Reclaimed material, max content: 50% by volume ▪ Quality requirements: <ul style="list-style-type: none"> – Aggregate for Class 1, Class 2, Class 3, and Class 4 aggregate subbases shall be clean and free from organic matter and other deleterious substances. – Class 4 aggregate shall conform to the grading and quality requirements set forth in the special provisions. – Aggregate for Class 5 aggregate subbases shall be selected from excavation at the locations designated. – Resistance (R-value), contract compliance: <ul style="list-style-type: none"> ▪ Class 1: ≥ 60 ▪ Class 2: ≥ 50 ▪ Class 3: ≥ 40 – Sand Equivalent: <ul style="list-style-type: none"> ▪ Operating range: ≥ 21 ▪ Contract compliance: ≥ 18 	<p>Subbase material:</p> <ul style="list-style-type: none"> ▪ Subbase material shall consist of hard durable particles or fragments of granular aggregates blended with fine sand, clay, stone dust, or other similar binding or filler materials. ▪ Quality requirements: <ul style="list-style-type: none"> – Free from vegetable matter, lumps or excessive amounts of clay, and other objectionable or foreign substances. ▪ Material passing the #40: <ul style="list-style-type: none"> – Liquid Limit ≤ 25 – Plasticity Index ≤ 6 ▪ Material finer than 0.02 mm shall be < 3%. ▪ Gradation Requirements: <table border="1" style="margin-left: 20px;"> <thead> <tr> <th>Sieve</th> <th>% Pass</th> </tr> </thead> <tbody> <tr> <td>3-in.</td> <td>100</td> </tr> <tr> <td>#10</td> <td>20 – 100</td> </tr> <tr> <td>#40</td> <td>5 – 60</td> </tr> <tr> <td>#200</td> <td>0 – 8</td> </tr> </tbody> </table> 	Sieve	% Pass	3-in.	100	#10	20 – 100	#40	5 – 60	#200	0 – 8
Sieve	% Pass											
3-in.	100											
#10	20 – 100											
#40	5 – 60											
#200	0 – 8											
Important Deviations	CALTRANS has no specific plasticity or gradation requirements.											
Level of Acceptability for Use	<ul style="list-style-type: none"> ▪ Group 2 – Except for plasticity index and aggregate gradation, the state-specified Class 1, Class 2, Class 3 material meets the FAA requirements. The state-specified Class 1, Class 2, and Class 3 material may be used on airfields supporting aircraft with less than 60,000 lbs maximum takeoff weight. ▪ Group 3 – The state-specified Class 1, Class 2, and Class 3 material may be used on FAA facilities if the FAA requirements for plasticity and gradation are met. ▪ Group 4 – The state-specified Class 4 and Class 5 material does not meet the requirements of the FAA item and are not acceptable for use on FAA facilities. <p>Note – FAA does not specify the use of recycled materials in subbase courses (see FAA Item P-219).</p>											

Item	SUBBASE COURSE							
	FAA and Caltrans Aggregate Gradation Requirements							
Additional Specifications	Gradation requirements:							
Sieve	FAA	Class 1		Class 2		Class 3		
		Operating Range	Contract Compliance	Operating Range	Contract Compliance	Operating Range	Contract Compliance	
3 in.	100	100	100	100	100	100	100	
2-1/2 in.	--	90 – 100	87 – 100	90 – 100	87 – 100	90 – 100	87 – 100	
#4	--	35 – 70	30 – 75	40 – 90	35 – 95	50 – 100	45 – 100	
#10	20 – 100	--	--	--	--	--	--	
#40	5 - 60	--	--	--	--	--	--	
#200	0 – 8	0 – 20	0 – 23	0 – 25	0 – 29	0 – 30	0 – 34	

Gradation plots comparing FAA to state agency gradation requirements:

P-154 Subbase Course

Sieve Size	P-154 (%)	CALTRANS, Class 1 (%)
#200	0	0
#40	5	15
#10	20	58
#4	60	70
3.0	100	100

Item	SUBBASE COURSE																																																							
	FAA and Caltrans Aggregate Gradation Requirements																																																							
Additional Specifications (Continued)	<p>Gradation plots comparing FAA to state agency gradation requirements:</p> <p>P-154 Subbase Course</p> <table border="1"> <caption>Data for P-154 Subbase Course Gradation Plot</caption> <thead> <tr> <th>Sieve Size</th> <th>P-154 (%)</th> <th>CALTRANS, Class 2 (%)</th> </tr> </thead> <tbody> <tr><td>#200</td><td>0</td><td>0</td></tr> <tr><td>#40</td><td>5</td><td>5</td></tr> <tr><td>#10</td><td>20</td><td>20</td></tr> <tr><td>#4</td><td>40</td><td>40</td></tr> <tr><td>0.375</td><td>60</td><td>60</td></tr> <tr><td>1.0</td><td>90</td><td>90</td></tr> <tr><td>2.0</td><td>100</td><td>100</td></tr> <tr><td>3.0</td><td>100</td><td>100</td></tr> </tbody> </table> <p>P-154 Subbase Course</p> <table border="1"> <caption>Data for P-154 Subbase Course Gradation Plot</caption> <thead> <tr> <th>Sieve Size</th> <th>P-154 (%)</th> <th>CALTRANS, Class 3 (%)</th> </tr> </thead> <tbody> <tr><td>#200</td><td>0</td><td>0</td></tr> <tr><td>#40</td><td>5</td><td>5</td></tr> <tr><td>#10</td><td>20</td><td>20</td></tr> <tr><td>#4</td><td>40</td><td>40</td></tr> <tr><td>0.375</td><td>60</td><td>60</td></tr> <tr><td>1.0</td><td>90</td><td>90</td></tr> <tr><td>2.0</td><td>100</td><td>100</td></tr> <tr><td>3.0</td><td>100</td><td>100</td></tr> </tbody> </table>		Sieve Size	P-154 (%)	CALTRANS, Class 2 (%)	#200	0	0	#40	5	5	#10	20	20	#4	40	40	0.375	60	60	1.0	90	90	2.0	100	100	3.0	100	100	Sieve Size	P-154 (%)	CALTRANS, Class 3 (%)	#200	0	0	#40	5	5	#10	20	20	#4	40	40	0.375	60	60	1.0	90	90	2.0	100	100	3.0	100	100
Sieve Size	P-154 (%)	CALTRANS, Class 2 (%)																																																						
#200	0	0																																																						
#40	5	5																																																						
#10	20	20																																																						
#4	40	40																																																						
0.375	60	60																																																						
1.0	90	90																																																						
2.0	100	100																																																						
3.0	100	100																																																						
Sieve Size	P-154 (%)	CALTRANS, Class 3 (%)																																																						
#200	0	0																																																						
#40	5	5																																																						
#10	20	20																																																						
#4	40	40																																																						
0.375	60	60																																																						
1.0	90	90																																																						
2.0	100	100																																																						
3.0	100	100																																																						

Item	LIME-TREATED SUBGRADE																	
	Caltrans	FAA																
Agency Specification	Section 24, Lime Stabilization	Item P-155, Lime-Treated Subgrade																
Description	This work shall consist of mixing lime and water with soil and compacting the mixture.	One or more courses of a mixture of soil, lime, and water.																
Test Methods Referenced	<ul style="list-style-type: none"> ASTM C977 	<ul style="list-style-type: none"> ASTM C977 																
Materials	<ul style="list-style-type: none"> Soil Lime Water 	<ul style="list-style-type: none"> Lime Water 																
Relevant Material Requirement(s)	<p>Lime: Lime shall conform to the requirements in ASTM C977, except that when a 250-gram test sample of quicklime is dry sieved in a mechanical sieve shaker for 10 minutes ± 30 seconds, it shall conform to the following grading requirements:</p> <table border="1"> <thead> <tr> <th>Sieve</th> <th>% Passing</th> </tr> </thead> <tbody> <tr> <td>3/8 in.</td> <td>98 – 100</td> </tr> <tr> <td>#100</td> <td>0 – 25</td> </tr> <tr> <td>#200</td> <td>0 – 14</td> </tr> </tbody> </table>	Sieve	% Passing	3/8 in.	98 – 100	#100	0 – 25	#200	0 – 14	<p>Lime:</p> <ul style="list-style-type: none"> Hydrated lime meeting ASTM C977 Commercial lime slurry consisting of hydrated lime meeting the following: <ul style="list-style-type: none"> Grade 1 "dry solids content" $\geq 31\%$ Grade 2 "dry solids content" $\geq 35\%$ Chemical composition, $\geq 70\%$ CaO and MgO <table border="1"> <thead> <tr> <th>Sieve</th> <th>Residue, % Retained</th> </tr> </thead> <tbody> <tr> <td>#6</td> <td>0.0</td> </tr> <tr> <td>#10</td> <td>≤ 1.0</td> </tr> <tr> <td>#30</td> <td>≤ 2.5</td> </tr> </tbody> </table> 	Sieve	Residue, % Retained	#6	0.0	#10	≤ 1.0	#30	≤ 2.5
Sieve	% Passing																	
3/8 in.	98 – 100																	
#100	0 – 25																	
#200	0 – 14																	
Sieve	Residue, % Retained																	
#6	0.0																	
#10	≤ 1.0																	
#30	≤ 2.5																	
Important Deviations	None																	
Level of Acceptability for Use	<ul style="list-style-type: none"> Group 1 – The state-specified material is equivalent to or exceeds the FAA specification. 																	

Item	AGGREGATE BASE COURSE	
	Caltrans	FAA
Agency Specification	Section 26, Aggregate Bases	Item P-208, Aggregate Base Course
Description	This work shall consist of furnishing, spreading, and compacting aggregate bases. Aggregate bases are designated as Class 2 or Class 3 (special provision only).	Base course composed of crushed or uncrushed aggregate bonded with either soil or fine aggregate or both.
Test Methods Referenced	<ul style="list-style-type: none"> • California Test 217 • California Test 229 • California Test 301 	<ul style="list-style-type: none"> • ASTM C29 • ASTM C88 • ASTM C131 • ASTM D4318
Materials	<ul style="list-style-type: none"> • Aggregate 	<ul style="list-style-type: none"> • Coarse aggregate • Filler material
Relevant Material Requirement(s)	<p>Aggregate:</p> <ul style="list-style-type: none"> • Aggregate may include material processed from reclaimed asphalt concrete, portland cement concrete, lean concrete base, cement-treated base, or a combination of these. <ul style="list-style-type: none"> – Reclaimed material, max content: 50% by volume • Quality requirements: <ul style="list-style-type: none"> – Aggregate for Class 2 aggregate base shall be free from organic matter and other deleterious substances. – Aggregate for Class 3 aggregate base shall conform to the requirements set forth in the CALTRANS special provisions: SSP 26-080 and SSP 26-100. – Resistance (R-value), contract compliance: <ul style="list-style-type: none"> ▪ Class 2: ≥ 78 ▪ Class 3: ≥ 50 – Sand Equivalent: <ul style="list-style-type: none"> ▪ Class 2 <ul style="list-style-type: none"> ▪ Operating range: ≥ 25 ▪ Contract compliance: ≥ 22 ▪ Class 3 <ul style="list-style-type: none"> ▪ Operating range: ≥ 21 ▪ Contract compliance: ≥ 18 – Durability Index (Class 2 only): <ul style="list-style-type: none"> ▪ Contract compliance: ≥ 18 	
Important Deviations	None	
Level of Acceptability for Use	<ul style="list-style-type: none"> • Group 2 – Except for aggregate gradation and ASTM C131, the state-specified material meets FAA material requirements. The state-specified material may be used on airfields supporting aircraft with less than 60,000 lbs maximum takeoff weight. • Group 3 – The state-specified material may be used on FAA facilities if the requirements for aggregate gradation and ASTM C131 are met. 	

Item	AGGREGATE BASE COURSE								
	FAA and Caltrans Aggregate Gradation Requirements								
Additional Specifications	Gradation requirements:								
	Sieve	% Passing							
		FAA Item P-208			CALTRANS				
					Aggregate Bases				
	Sieve	2-in. max	1 1/2-in. max	1-in. max	Class 2		Class 3		
					1 1/2-in. max	3/4-in. max	SSP 06-080	SSP 06-100	
	2 in.	100	--	--	100	--	100	--	--
	1-1/2 in.	70 – 100	100	--	87 – 100	--	87 – 100	--	--
	1 in.	55 – 85	70 – 100	100	--	100	--	100	100
	3/4 in.	50 – 80	55 – 85	70 – 100	45 – 90	87 – 100	45 – 95	87 – 100	87 – 100
	#4	30 – 60	30 – 60	35 – 65	20 – 50	30 – 65	20 – 65	35 – 75	30 – 65
	#30	--	--	--	6 – 29	5 – 35	6 – 39	7 – 45	5 – 35
	#40	10 – 30	10 – 30	10 – 25	--	--	--	--	--
	#200	5 – 15	5 – 15	5 – 15	0 – 12	0 – 12	0 – 19	0 – 19	0 – 12
	#200 (frost areas)	0 – 8	0 – 8	0 – 8	Hatched				

Item	AGGREGATE BASE COURSE																																																																								
	FAA and Caltrans Aggregate Gradation Requirements																																																																								
Additional Specifications (Continued)	<p>Gradation plots comparing FAA to state agency gradation requirements:</p> <p>P-208 Aggregate Base Course</p> <table border="1"> <caption>Data for P-208 Aggregate Base Course (Sieve Size)</caption> <thead> <tr> <th>Sieve Size</th> <th>P-208, 1 in. (%)</th> <th>P-208, 1 in. (areas of frost) (%)</th> <th>CALTRANS, Class 2, 3/4 in. max (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#40</td> <td>10</td> <td>25</td> <td>0</td> </tr> <tr> <td>#30</td> <td>12</td> <td>0</td> <td>5</td> </tr> <tr> <td>#4</td> <td>35</td> <td>0</td> <td>30</td> </tr> <tr> <td>0.75</td> <td>70</td> <td>0</td> <td>90</td> </tr> <tr> <td>1.0</td> <td>100</td> <td>0</td> <td>100</td> </tr> <tr> <td>1.5</td> <td>0</td> <td>0</td> <td>85</td> </tr> <tr> <td>2.0</td> <td>0</td> <td>0</td> <td>0</td> </tr> </tbody> </table> <p>P-208 Aggregate Base Course</p> <table border="1"> <caption>Data for P-208 Aggregate Base Course (Sieve Size)</caption> <thead> <tr> <th>Sieve Size</th> <th>P-208, 2 in. (%)</th> <th>P-208, 2 in. (areas of frost) (%)</th> <th>CALTRANS, Class 2, 1 1/2 in. max (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#40</td> <td>10</td> <td>28</td> <td>0</td> </tr> <tr> <td>#30</td> <td>12</td> <td>0</td> <td>5</td> </tr> <tr> <td>#4</td> <td>30</td> <td>0</td> <td>20</td> </tr> <tr> <td>0.75</td> <td>50</td> <td>0</td> <td>90</td> </tr> <tr> <td>1.0</td> <td>80</td> <td>0</td> <td>100</td> </tr> <tr> <td>1.5</td> <td>70</td> <td>0</td> <td>85</td> </tr> <tr> <td>2.0</td> <td>100</td> <td>0</td> <td>0</td> </tr> </tbody> </table>	Sieve Size	P-208, 1 in. (%)	P-208, 1 in. (areas of frost) (%)	CALTRANS, Class 2, 3/4 in. max (%)	#200	0	0	0	#40	10	25	0	#30	12	0	5	#4	35	0	30	0.75	70	0	90	1.0	100	0	100	1.5	0	0	85	2.0	0	0	0	Sieve Size	P-208, 2 in. (%)	P-208, 2 in. (areas of frost) (%)	CALTRANS, Class 2, 1 1/2 in. max (%)	#200	0	0	0	#40	10	28	0	#30	12	0	5	#4	30	0	20	0.75	50	0	90	1.0	80	0	100	1.5	70	0	85	2.0	100	0	0
Sieve Size	P-208, 1 in. (%)	P-208, 1 in. (areas of frost) (%)	CALTRANS, Class 2, 3/4 in. max (%)																																																																						
#200	0	0	0																																																																						
#40	10	25	0																																																																						
#30	12	0	5																																																																						
#4	35	0	30																																																																						
0.75	70	0	90																																																																						
1.0	100	0	100																																																																						
1.5	0	0	85																																																																						
2.0	0	0	0																																																																						
Sieve Size	P-208, 2 in. (%)	P-208, 2 in. (areas of frost) (%)	CALTRANS, Class 2, 1 1/2 in. max (%)																																																																						
#200	0	0	0																																																																						
#40	10	28	0																																																																						
#30	12	0	5																																																																						
#4	30	0	20																																																																						
0.75	50	0	90																																																																						
1.0	80	0	100																																																																						
1.5	70	0	85																																																																						
2.0	100	0	0																																																																						

Item	AGGREGATE BASE COURSE																																																		
	FAA and Caltrans Aggregate Gradation Requirements																																																		
Additional Specifications (Continued)	<p>P-208 Aggregate Base Course</p> <table border="1"> <caption>P-208 Aggregate Base Course Gradation Data</caption> <thead> <tr> <th>Sieve Size (mm)</th> <th>P-208, 1 in. (%)</th> <th>P-208, 1 in. (areas of frost) (%)</th> <th>CALTRANS, Class 3, SSP 06-080 (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#40 #30</td> <td>10</td> <td>25</td> <td>5</td> </tr> <tr> <td>#4</td> <td>35</td> <td>65</td> <td>35</td> </tr> <tr> <td>0.75</td> <td>70</td> <td>100</td> <td>90</td> </tr> <tr> <td>1.0</td> <td>100</td> <td>100</td> <td>100</td> </tr> </tbody> </table> <p>P-208 Aggregate Base Course</p> <table border="1"> <caption>P-208 Aggregate Base Course Gradation Data</caption> <thead> <tr> <th>Sieve Size (mm)</th> <th>P-208, 1 in. (%)</th> <th>P-208, 1 in. (areas of frost) (%)</th> <th>CALTRANS, Class 3, SSP 06-100 (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#40 #30</td> <td>10</td> <td>25</td> <td>5</td> </tr> <tr> <td>#4</td> <td>35</td> <td>65</td> <td>30</td> </tr> <tr> <td>0.75</td> <td>70</td> <td>100</td> <td>85</td> </tr> <tr> <td>1.0</td> <td>100</td> <td>100</td> <td>100</td> </tr> </tbody> </table>	Sieve Size (mm)	P-208, 1 in. (%)	P-208, 1 in. (areas of frost) (%)	CALTRANS, Class 3, SSP 06-080 (%)	#200	0	0	0	#40 #30	10	25	5	#4	35	65	35	0.75	70	100	90	1.0	100	100	100	Sieve Size (mm)	P-208, 1 in. (%)	P-208, 1 in. (areas of frost) (%)	CALTRANS, Class 3, SSP 06-100 (%)	#200	0	0	0	#40 #30	10	25	5	#4	35	65	30	0.75	70	100	85	1.0	100	100	100		
Sieve Size (mm)	P-208, 1 in. (%)	P-208, 1 in. (areas of frost) (%)	CALTRANS, Class 3, SSP 06-080 (%)																																																
#200	0	0	0																																																
#40 #30	10	25	5																																																
#4	35	65	35																																																
0.75	70	100	90																																																
1.0	100	100	100																																																
Sieve Size (mm)	P-208, 1 in. (%)	P-208, 1 in. (areas of frost) (%)	CALTRANS, Class 3, SSP 06-100 (%)																																																
#200	0	0	0																																																
#40 #30	10	25	5																																																
#4	35	65	30																																																
0.75	70	100	85																																																
1.0	100	100	100																																																

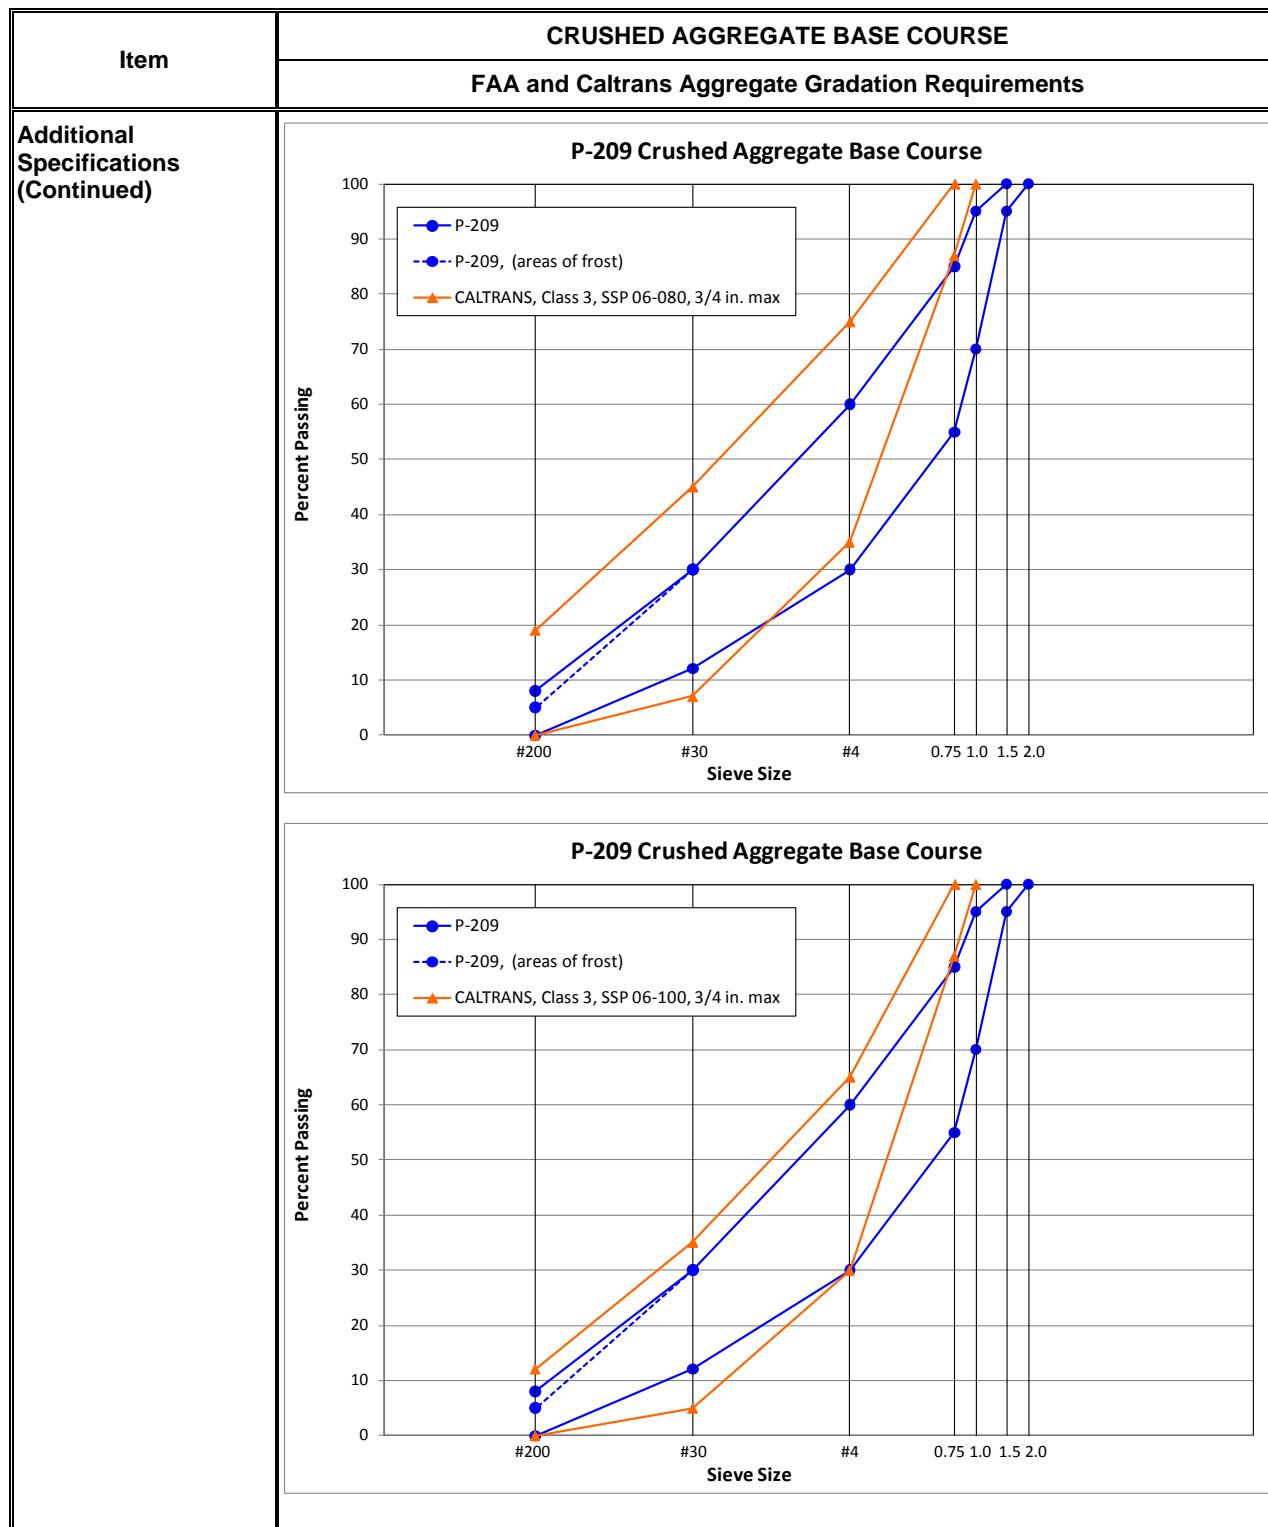
Item	AGGREGATE BASE COURSE
	FAA and Caltrans Aggregate Gradation Requirements
Additional Specifications (Continued)	<p>P-208 Aggregate Base Course</p> <p>The graph plots Percent Passing (Y-axis, 0 to 100) against Sieve Size (X-axis, #200, #40 #30, #4, 0.75, 1.0, 1.5, 2.0). Three data series are shown:</p> <ul style="list-style-type: none"> P-208, 2 in. (Solid Blue Line with Circles): Starts at ~15% at #200, rises to ~30% at #40 #30, ~60% at #4, ~85% at 0.75, and reaches 100% at 1.0. P-208, 2 in. (areas of frost) (Dashed Blue Line with Circles): Starts at ~5% at #200, rises to ~10% at #40 #30, ~30% at #4, ~55% at 0.75, and reaches 100% at 1.5. CALTRANS, Class 3, SSP 06-080, 1 1/2 in. max (Solid Orange Line with Triangles): Starts at 0% at #200, rises to ~5% at #40 #30, ~20% at #4, ~45% at 0.75, and reaches 100% at 1.5.

Item	CRUSHED AGGREGATE BASE COURSE	
	Caltrans	FAA
Agency Specification	Section 26, Aggregate Bases	Item P-209, Crushed Aggregate Base Course
Description	This work shall consist of furnishing, spreading, and compacting aggregate bases. Aggregate bases are designated as Class 2 or Class 3 (special provision only).	Base course composed of crushed aggregate.
Test Methods Referenced	<ul style="list-style-type: none"> California Test 217 California Test 229 California Test 301 	<ul style="list-style-type: none"> ASTM C29 ASTM C88 ASTM C131 ASTM D2419 ASTM D4318
Materials	<ul style="list-style-type: none"> Aggregate 	<ul style="list-style-type: none"> Crushed coarse aggregate
Relevant Material Requirement(s)	<p>Aggregate:</p> <ul style="list-style-type: none"> Aggregate may include material processed from reclaimed asphalt concrete, portland cement concrete, lean concrete base, cement-treated base, or a combination. <ul style="list-style-type: none"> Reclaimed material, max content: 50% by volume Quality requirements: <ul style="list-style-type: none"> Aggregate for Class 2 aggregate base shall be free from organic matter and other deleterious substances. Aggregate for Class 3 aggregate base shall conform to the requirements set forth in the CALTRANS special provisions: SSP 26-080 and SSP 26-100. Resistance (R-value), contract compliance: <ul style="list-style-type: none"> Class 2: ≥ 78 Class 3: ≥ 50 Sand Equivalent: <ul style="list-style-type: none"> Class 2 <ul style="list-style-type: none"> Operating range: ≥ 25 Contract compliance: ≥ 22 Class 3 <ul style="list-style-type: none"> Operating range: ≥ 21 Contract compliance: ≥ 18 Durability Index (Class 2 only): <ul style="list-style-type: none"> Contract compliance: ≥ 18 	
Important Deviations	None	
Level of Acceptability for Use	<ul style="list-style-type: none"> Group 2 – Except for aggregate gradation, percent fractured faces, ASTM C88, ASTM C131, and ASTM D4318, the state-specified Class 2 1-1/2 in. and Class 3 SSP 06-080 1-1/2 in. material meets FAA material requirements. The state-specified material may be used on airfields supporting aircraft with less than 60,000 lbs maximum takeoff weight. Group 3 – The state-specified Class 2 1-1/2 in. and Class 3 SSP 06-080 1-1/2 in. material may be used on FAA facilities if the requirements for aggregate gradation, percent fractured faces, ASTM C88, ASTM C131, and ASTM D4318 are met. Group 4 – The state-specified Class 3 SSP 06-080 3/4 in. and Class 3 SSP 06-100 3/4 in. material is unable to meet FAA aggregate gradation requirements and therefore is not acceptable for use on FAA facilities. 	

Item	CRUSHED AGGREGATE BASE COURSE						
	FAA and Caltrans Aggregate Gradation Requirements						
Additional Specifications	Gradation requirements:						
	Sieve	% Passing					
		FAA Item P-209	CALTRANS				
			Aggregate Bases				
	Design	Class 2		Class 3			
		1 1/2-in. max	3/4-in. max	SSP 06-080	SSP 06-100	3/4-in. max	
	2 in.	100	100	--	100	--	--
	1-1/2 in.	95 – 100	87 – 100	--	87 – 100	--	--
	1 in.	70 – 95	--	100	--	100	100
	3/4 in.	55 – 85	45 – 90	87 – 100	45 – 95	87 – 100	87 – 100
	#4	30 – 60	20 – 50	30 – 65	20 – 65	35 – 75	30 – 65
	#30	12 – 30	6 – 29	5 – 35	6 – 39	7 – 45	5 – 35
	#200	0 – 8 ⁹	0 – 12	0 – 12	0 – 19	0 – 19	0 – 12
	#200 (frost areas)	0 – 5 ⁹	/				

⁹ The fraction passing the #200 shall be ≤ 60% of that passing the #30.

Item	CRUSHED AGGREGATE BASE COURSE																																																																
	FAA and Caltrans Aggregate Gradation Requirements																																																																
Additional Specifications (Continued)	<p>Gradation plots comparing FAA to state agency gradation requirements:</p> <p>P-209 Crushed Aggregate Base Course</p> <table border="1"> <caption>Data for P-209 Crushed Aggregate Base Course Gradation Plot</caption> <thead> <tr> <th>Sieve Size</th> <th>P-209 (%)</th> <th>P-209 (areas of frost) (%)</th> <th>CALTRANS (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#30</td> <td>12</td> <td>30</td> <td>5</td> </tr> <tr> <td>#4</td> <td>60</td> <td>30</td> <td>30</td> </tr> <tr> <td>0.75</td> <td>55</td> <td>85</td> <td>100</td> </tr> <tr> <td>1.0</td> <td>70</td> <td>100</td> <td>100</td> </tr> <tr> <td>1.5</td> <td>95</td> <td>100</td> <td>100</td> </tr> <tr> <td>2.0</td> <td>100</td> <td>100</td> <td>100</td> </tr> </tbody> </table> <p>P-209 Crushed Aggregate Base Course</p> <table border="1"> <caption>Data for P-209 Crushed Aggregate Base Course Gradation Plot</caption> <thead> <tr> <th>Sieve Size</th> <th>P-209 (%)</th> <th>P-209 (areas of frost) (%)</th> <th>CALTRANS (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#30</td> <td>12</td> <td>30</td> <td>30</td> </tr> <tr> <td>#4</td> <td>60</td> <td>30</td> <td>20</td> </tr> <tr> <td>0.75</td> <td>55</td> <td>95</td> <td>100</td> </tr> <tr> <td>1.0</td> <td>70</td> <td>100</td> <td>100</td> </tr> <tr> <td>1.5</td> <td>95</td> <td>100</td> <td>100</td> </tr> <tr> <td>2.0</td> <td>100</td> <td>100</td> <td>100</td> </tr> </tbody> </table>	Sieve Size	P-209 (%)	P-209 (areas of frost) (%)	CALTRANS (%)	#200	0	0	0	#30	12	30	5	#4	60	30	30	0.75	55	85	100	1.0	70	100	100	1.5	95	100	100	2.0	100	100	100	Sieve Size	P-209 (%)	P-209 (areas of frost) (%)	CALTRANS (%)	#200	0	0	0	#30	12	30	30	#4	60	30	20	0.75	55	95	100	1.0	70	100	100	1.5	95	100	100	2.0	100	100	100
Sieve Size	P-209 (%)	P-209 (areas of frost) (%)	CALTRANS (%)																																																														
#200	0	0	0																																																														
#30	12	30	5																																																														
#4	60	30	30																																																														
0.75	55	85	100																																																														
1.0	70	100	100																																																														
1.5	95	100	100																																																														
2.0	100	100	100																																																														
Sieve Size	P-209 (%)	P-209 (areas of frost) (%)	CALTRANS (%)																																																														
#200	0	0	0																																																														
#30	12	30	30																																																														
#4	60	30	20																																																														
0.75	55	95	100																																																														
1.0	70	100	100																																																														
1.5	95	100	100																																																														
2.0	100	100	100																																																														



Item	CRUSHED AGGREGATE BASE COURSE																																
	FAA and Caltrans Aggregate Gradation Requirements																																
Additional Specifications (Continued)	<p style="text-align: center;">P-209 Crushed Aggregate Base Course</p> <p>Percent Passing</p> <p>Sieve Size</p> <table border="1"> <caption>Data points estimated from the gradation curve graph</caption> <thead> <tr> <th>Sieve Size</th> <th>P-209 (%)</th> <th>P-209 (areas of frost) (%)</th> <th>CALTRANS (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#30</td> <td>12</td> <td>10</td> <td>6</td> </tr> <tr> <td>#4</td> <td>30</td> <td>28</td> <td>20</td> </tr> <tr> <td>0.75</td> <td>55</td> <td>53</td> <td>45</td> </tr> <tr> <td>1.0</td> <td>70</td> <td>68</td> <td>95</td> </tr> <tr> <td>1.5</td> <td>95</td> <td>93</td> <td>98</td> </tr> <tr> <td>2.0</td> <td>100</td> <td>100</td> <td>100</td> </tr> </tbody> </table>	Sieve Size	P-209 (%)	P-209 (areas of frost) (%)	CALTRANS (%)	#200	0	0	0	#30	12	10	6	#4	30	28	20	0.75	55	53	45	1.0	70	68	95	1.5	95	93	98	2.0	100	100	100
Sieve Size	P-209 (%)	P-209 (areas of frost) (%)	CALTRANS (%)																														
#200	0	0	0																														
#30	12	10	6																														
#4	30	28	20																														
0.75	55	53	45																														
1.0	70	68	95																														
1.5	95	93	98																														
2.0	100	100	100																														

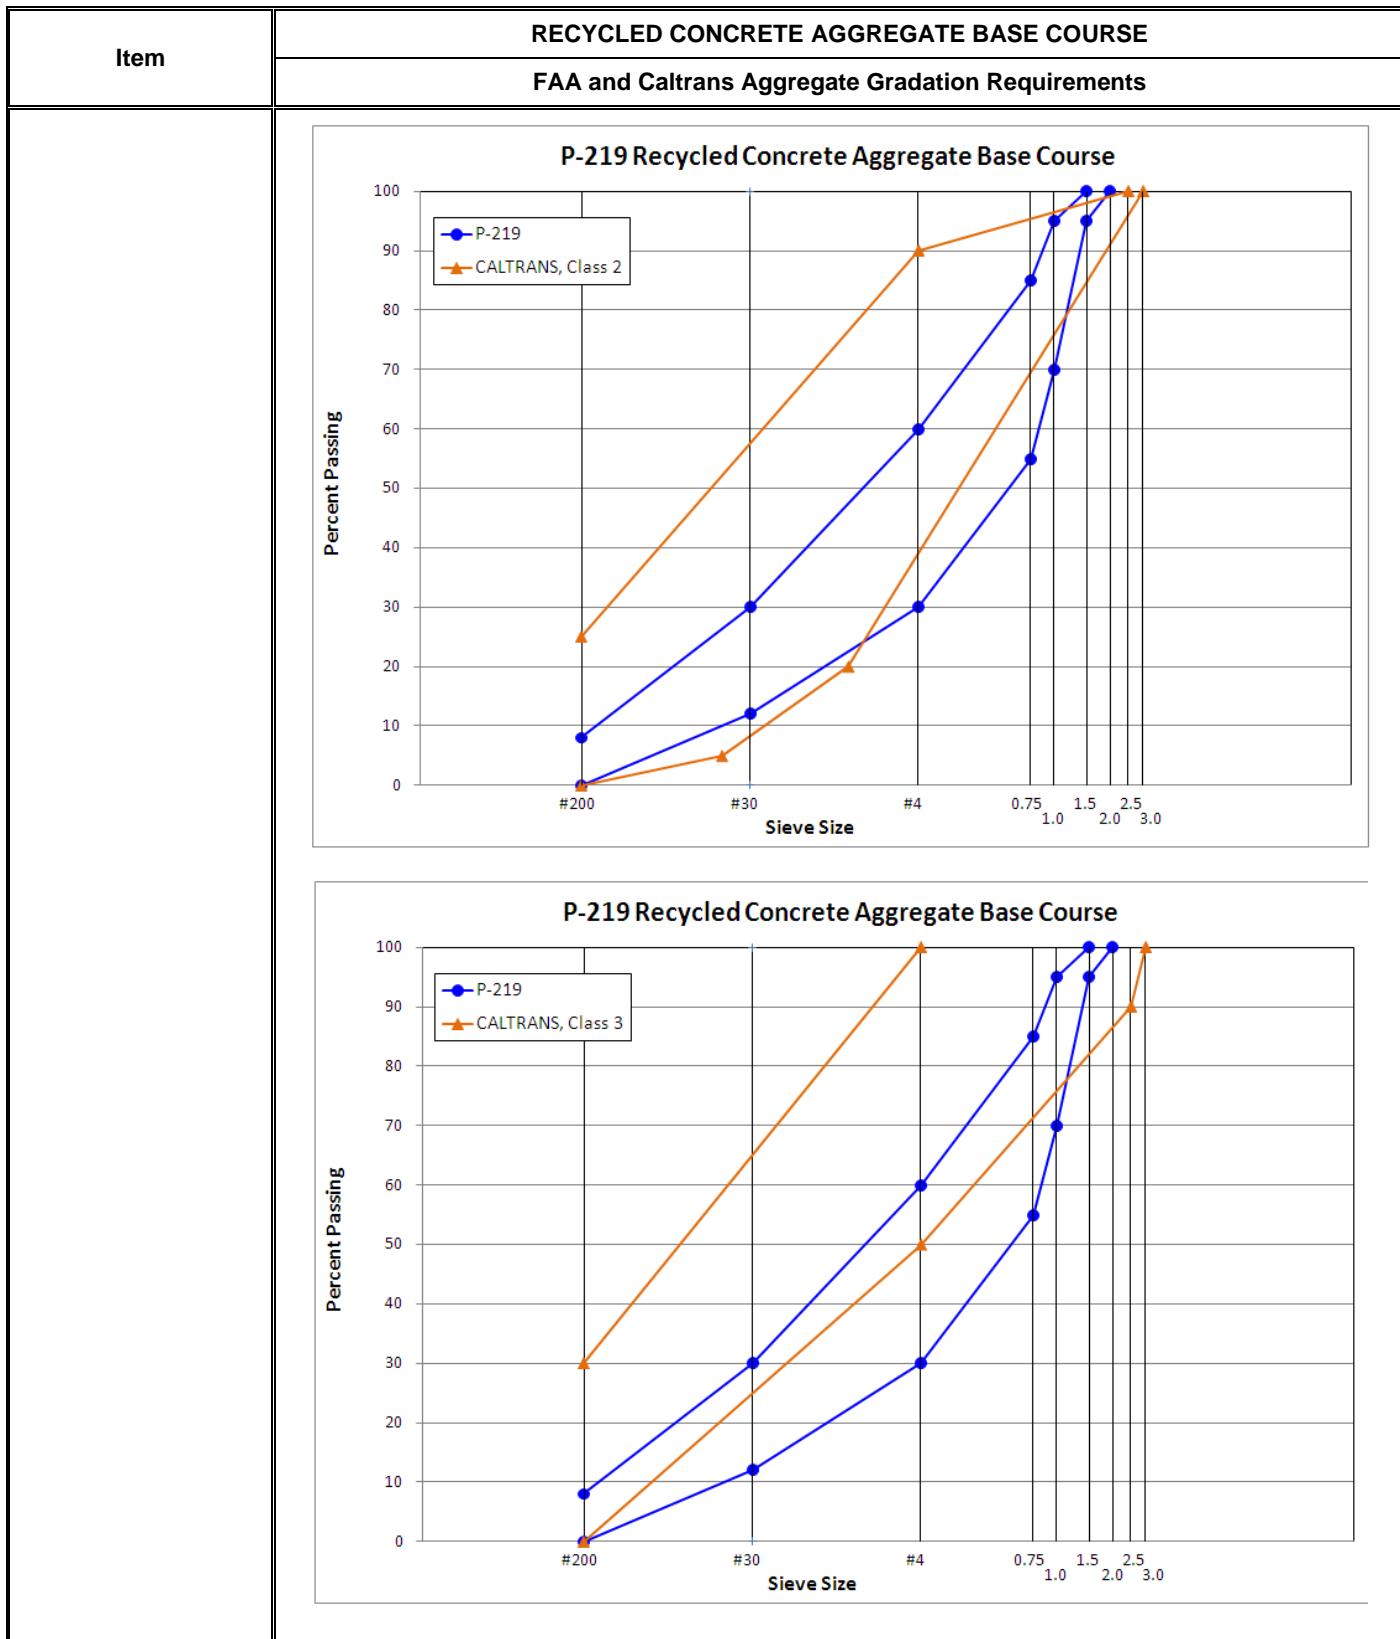
Item	RECYCLED CONCRETE AGGREGATE BASE COURSE									
	CALTRANS	FAA								
Agency Specification	Section 25, Aggregate Subbases	Item P-219, Recycled Concrete Aggregate Base Course								
Description	This work shall consist of furnishing, spreading, and compacting aggregate subbases. Aggregate subbases are designated as Class 1, Class 2, Class 3, Class 4, or Class 5.	Base course composed of recycled concrete aggregate, crushed to meet a particular gradation.								
Test Methods Referenced	<ul style="list-style-type: none"> ▪ California Test 217 ▪ California Test 301 	<ul style="list-style-type: none"> ▪ ASTM C131 ▪ ASTM D2419 ▪ ASTM D4318 								
Materials	<ul style="list-style-type: none"> ▪ Aggregate 	<ul style="list-style-type: none"> ▪ Recycled concrete aggregate ▪ Fine aggregate 								
Relevant Material Requirement(s)	<p>Coarse aggregate:</p> <ul style="list-style-type: none"> ▪ Aggregate may include material processed from reclaimed asphalt concrete, portland cement concrete, lean concrete base, cement-treated base, or a combination of these. <ul style="list-style-type: none"> – Reclaimed material, max content: 50% by volume ▪ Quality requirements: <ul style="list-style-type: none"> – Aggregate for Class 1, Class 2, Class 3, and Class 4 aggregate subbases shall be clean and free from organic matter and other deleterious substances. – Class 4 aggregate shall conform to the grading and quality requirements set forth in the special provisions. – Aggregate for Class 5 aggregate subbases shall be selected from excavation at the locations designated. – Resistance (R-value), contract compliance: <ul style="list-style-type: none"> ▪ Class 1: ≥ 60 ▪ Class 2: ≥ 50 ▪ Class 3: ≥ 40 – Sand Equivalent: <ul style="list-style-type: none"> ▪ Operating range: ≥ 21 ▪ Contract compliance: ≥ 18 	<p>Recycled concrete aggregate:</p> <ul style="list-style-type: none"> ▪ Recycled concrete aggregate shall consist of $\geq 90\%$ PCC (with virgin aggregate added if necessary), with the following making up the remaining: <table border="1" style="margin-left: 20px;"> <thead> <tr> <th>Material</th> <th>Max Content</th> </tr> </thead> <tbody> <tr> <td>Wood</td> <td>0.1%</td> </tr> <tr> <td>Brick, mica, schist, or other friable material</td> <td>4%</td> </tr> <tr> <td>Asphalt Concrete</td> <td>10%</td> </tr> </tbody> </table> <ul style="list-style-type: none"> ▪ Quality requirements: <ul style="list-style-type: none"> ○ Wear (ASTM C131), max loss: 45% ○ Material passing the #40: <ul style="list-style-type: none"> ▪ Liquid Limit ≤ 25 ▪ Plasticity Index ≤ 4 <p>Fine aggregate:</p> <ul style="list-style-type: none"> ▪ Fine aggregate shall be fines produced from the crushing operation. ▪ Sand equivalent value ≥ 35 (ASTM D2419) 	Material	Max Content	Wood	0.1%	Brick, mica, schist, or other friable material	4%	Asphalt Concrete	10%
Material	Max Content									
Wood	0.1%									
Brick, mica, schist, or other friable material	4%									
Asphalt Concrete	10%									
Important Deviations										
Level of Acceptability for Use	<ul style="list-style-type: none"> ▪ Group 2 – Except for aggregate gradation, ASTM C131, ASTM D2419, and ASTM D4318, the state-specified material meets FAA material requirements. The state-specified material may be used on airfields supporting aircraft with less than 60,000 lbs maximum takeoff weight. ▪ Group 3 – The state-specified material may be used on FAA facilities if the requirements for aggregate gradation, ASTM C131, ASTM D2419, and ASTM D4318 are met. <p>Note – FAA requires that $\geq 90\%$ of aggregate shall consist of recycled PCC.</p>									

Item	RECYCLED CONCRETE AGGREGATE BASE COURSE							
	FAA and Caltrans Aggregate Gradation Requirements							
Additional Specifications	Sieve	FAA	% Passing					
			Class 1		Class 2		Class 3	
	3 in.		Operating Range	Contract Compliance	Operating Range	Contract Compliance	Operating Range	Contract Compliance
	3 in.		100	100	100	100	100	100
	2-1/2 in.		90 – 100	87 – 100	90 – 100	87 – 100	90 – 100	87 – 100
	2 in.	100						
	1-1/2 in.	95 – 100						
	1 in.	70 – 95						
	3/4 in.	55 – 85						
	#4	30 – 60	35 – 70	30 – 75	40 – 90	35 – 95	50 – 100	45 – 100
	#30	12 – 30						
	#200	0 – 8	0 – 20	0 – 23	0 – 25	0 – 29	0 – 30	0 – 34

Gradation plots comparing FAA to state agency gradation requirements:

P-219 Recycled Concrete Aggregate Base Course

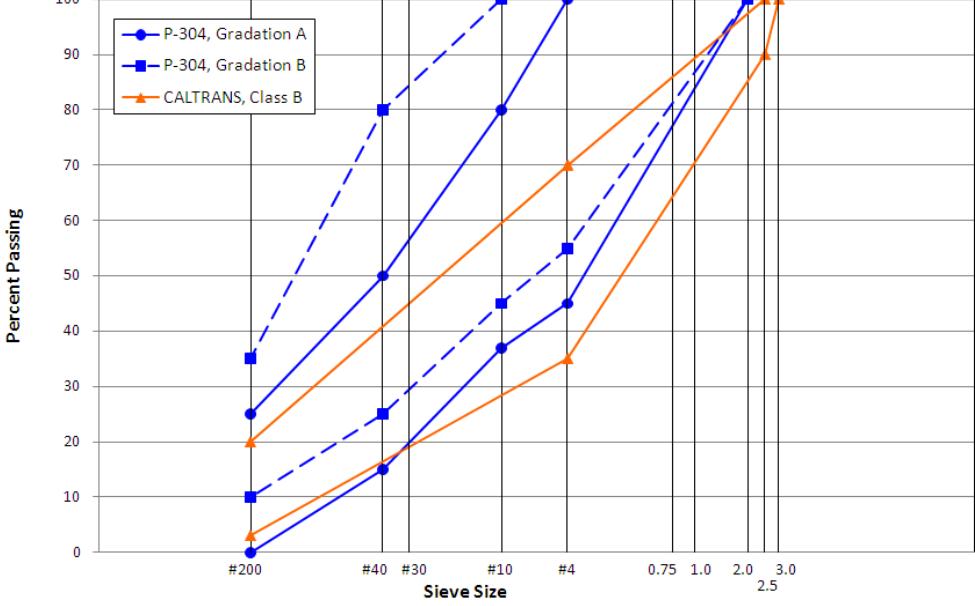
Sieve Size	P-219 (%)	CALTRANS, Class 1 (%)
#200	8	0
#30	12	10
#4	30	35
0.75	55	70
1.0	70	85
1.5	95	90
2.0	98	95
2.5	100	100
3.0	100	100



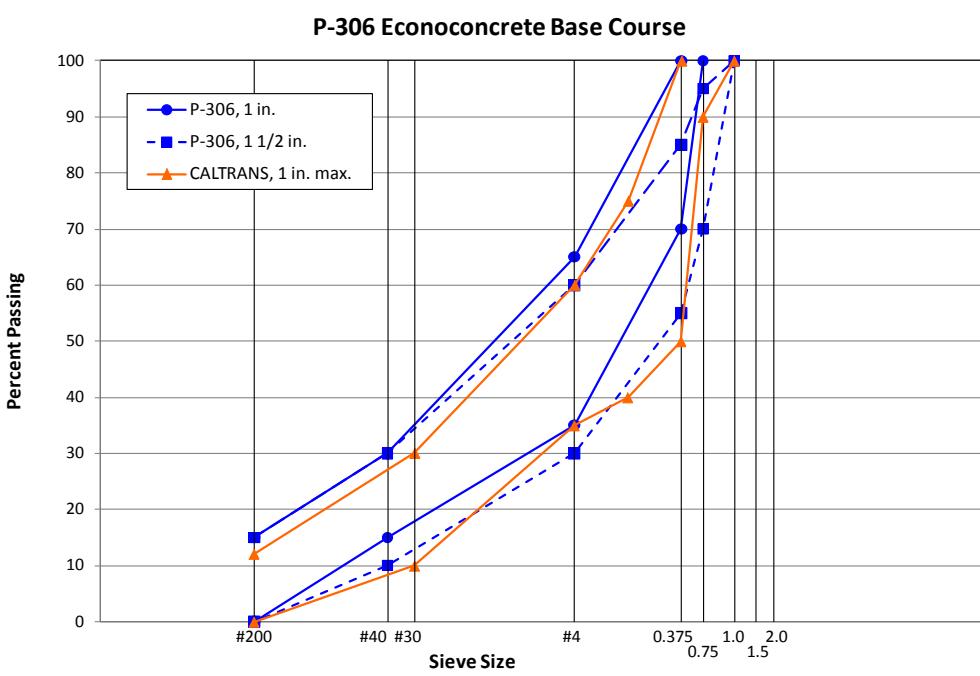
Item	CEMENT-TREATED BASE COURSE	
	Caltrans	FAA
Agency Specification	Section 27, Cement Treated Bases	Item P-304, Cement-Treated Base Course
Description	This work shall consist of furnishing and mixing aggregate, cement and water, and spreading and compacting the mixture. Cement-treated bases are designated as Class A or Class B, and as road-mixed or plant-mixed.	Base course composed of uniformly mixed mineral aggregate, cement, and water.
Test Methods Referenced	<ul style="list-style-type: none"> ▪ ASTM C150 ▪ California Test 312 ▪ California Test 527 	<ul style="list-style-type: none"> ▪ ASTM C88 ▪ ASTM C131 ▪ ASTM C150 or ASTM C595 ▪ ASTM C618 ▪ ASTM C989 ▪ ASTM D4318
Materials	<ul style="list-style-type: none"> ▪ Portland cement (Type II Modified) ▪ Aggregate ▪ Water 	<ul style="list-style-type: none"> ▪ Aggregate ▪ Cement ▪ Cementitious additives ▪ Water ▪ Curing materials ▪ Sand blotter
Relevant Material Requirement(s)	<p>Aggregate:</p> <ul style="list-style-type: none"> ▪ Aggregate for Class A cement-treated base shall be of such quality that when mixed with Type II Modified portland cement in an amount \leq 5% by weight of dry aggregate and compacted at optimum moisture content, the compressive strength of the compacted mixture is \geq 750 psi at 7 days, determined according to California Test 312. ▪ Aggregate for Class B cement-treated base shall have a Resistance (R-value) \geq 60 before mixing with Type II Modified portland cement, and a R-value \geq 80 after mixing with Type II Modified portland cement in an amount \leq 2.5% by weight of dry aggregate. ▪ Quality requirements: <ul style="list-style-type: none"> – Sand Equivalent <ul style="list-style-type: none"> ▪ Operating range: \geq 21 ▪ Contract compliance: \geq 18 – Clean and free from vegetation and other deleterious substances. <p>Portland cement:</p> <ul style="list-style-type: none"> ▪ Type II Modified portland cement meeting ASTM C150 and the following: <ul style="list-style-type: none"> – Equivalent alkalis, max content: 0.60% – Autoclave expansion: \leq 0.50% – Mortar, containing the cement to be used and Ottawa silica sand, when tested according to California Test 527, shall not expand in water $>$ 0.010% and shall not contract in air $>$ 0.048%. 	<p>Aggregate:</p> <ul style="list-style-type: none"> ▪ Crushed or uncrushed gravel, crushed stone, or crushed PCC ▪ Crushed aggregate quality requirements: <ul style="list-style-type: none"> – Soundness (ASTM C88), max loss: <ul style="list-style-type: none"> ▪ Sodium sulfate, 10% ▪ Magnesium sulfate, 13% – Wear (ASTM C131), max loss: 40% ▪ Material passing the #40: <ul style="list-style-type: none"> – Liquid Limit \leq 25 – Plasticity Index \leq 6 <p>Portland cement:</p> <ul style="list-style-type: none"> ▪ Type I, II, III, IV, or V portland cement meeting ASTM C150. ▪ Type IS, IS-A, IP, IP-A, P, or PA blended cement meeting ASTM C595. <p>Pozzolan materials:</p> <ul style="list-style-type: none"> ▪ Class C, F, or N meeting ASTM C618 ▪ Max 6% LOI for Classes F and N. <p>Ground granulated blast furnace slag:</p> <ul style="list-style-type: none"> ▪ Grade 80, 100, or 120 meeting ASTM C989.
Important Deviations	CALTRANS has no specific requirement for plasticity or liquid limit.	

Item	CEMENT-TREATED BASE COURSE	
	Caltrans	FAA
Level of Acceptability for Use	<ul style="list-style-type: none"> Group 2 – The state material specification does not include provisions for ASTM C88 or ASTM D4318. The state-specified material may be used on airfields supporting aircraft with less than 60,000 lbs maximum takeoff weight. Group 3 – The state-specified material may be used on FAA facilities if the requirements for aggregate gradation, ASTM C88, and ASTM D4318 are met. 	

Item	CEMENT-TREATED BASE COURSE																																																																																															
	FAA and Caltrans Aggregate Gradation Requirements																																																																																															
Additional Specifications	Gradation requirements: <table border="1"> <thead> <tr> <th rowspan="3">Sieve</th> <th colspan="6">% Passing</th> </tr> <tr> <th colspan="2">FAA</th> <th colspan="4">CALTRANS</th> </tr> <tr> <th>Gradation A</th> <th>Gradation B</th> <th>Operating Range</th> <th>Contract Compliance</th> <th>Operating Range</th> <th>Contract Compliance</th> </tr> </thead> <tbody> <tr> <td>3 in.</td> <td>--</td> <td>--</td> <td>--</td> <td>--</td> <td>100</td> <td>100</td> </tr> <tr> <td>2-1/2 in.</td> <td>--</td> <td>--</td> <td>--</td> <td>--</td> <td>90 – 100</td> <td>87 – 100</td> </tr> <tr> <td>2 in.</td> <td>100¹⁰</td> <td>100¹⁰</td> <td>--</td> <td>--</td> <td>--</td> <td>--</td> </tr> <tr> <td>1 in.</td> <td>--</td> <td>--</td> <td>100</td> <td>100</td> <td>--</td> <td>--</td> </tr> <tr> <td>3/4 in.</td> <td>--</td> <td>--</td> <td>90 – 100</td> <td>87 – 100</td> <td>--</td> <td>--</td> </tr> <tr> <td>#4</td> <td>45 – 100</td> <td>55 – 100</td> <td>40 – 70</td> <td>35 – 75</td> <td>35 – 70</td> <td>28 – 77</td> </tr> <tr> <td>#10</td> <td>37 – 80</td> <td>45 – 100</td> <td>--</td> <td>--</td> <td>--</td> <td>--</td> </tr> <tr> <td>#30</td> <td>--</td> <td>--</td> <td>12 – 40</td> <td>7 – 45</td> <td>--</td> <td>--</td> </tr> <tr> <td>#40</td> <td>15 – 50</td> <td>25 – 80</td> <td>--</td> <td>--</td> <td>--</td> <td>--</td> </tr> <tr> <td>#200</td> <td>0 – 25</td> <td>10 – 35</td> <td>3 – 15</td> <td>0 – 19</td> <td>3 – 20</td> <td>0 – 24</td> </tr> </tbody> </table>							Sieve	% Passing						FAA		CALTRANS				Gradation A	Gradation B	Operating Range	Contract Compliance	Operating Range	Contract Compliance	3 in.	--	--	--	--	100	100	2-1/2 in.	--	--	--	--	90 – 100	87 – 100	2 in.	100 ¹⁰	100 ¹⁰	--	--	--	--	1 in.	--	--	100	100	--	--	3/4 in.	--	--	90 – 100	87 – 100	--	--	#4	45 – 100	55 – 100	40 – 70	35 – 75	35 – 70	28 – 77	#10	37 – 80	45 – 100	--	--	--	--	#30	--	--	12 – 40	7 – 45	--	--	#40	15 – 50	25 – 80	--	--	--	--	#200	0 – 25	10 – 35	3 – 15	0 – 19	3 – 20	0 – 24
Sieve	% Passing																																																																																															
	FAA		CALTRANS																																																																																													
	Gradation A	Gradation B	Operating Range	Contract Compliance	Operating Range	Contract Compliance																																																																																										
3 in.	--	--	--	--	100	100																																																																																										
2-1/2 in.	--	--	--	--	90 – 100	87 – 100																																																																																										
2 in.	100 ¹⁰	100 ¹⁰	--	--	--	--																																																																																										
1 in.	--	--	100	100	--	--																																																																																										
3/4 in.	--	--	90 – 100	87 – 100	--	--																																																																																										
#4	45 – 100	55 – 100	40 – 70	35 – 75	35 – 70	28 – 77																																																																																										
#10	37 – 80	45 – 100	--	--	--	--																																																																																										
#30	--	--	12 – 40	7 – 45	--	--																																																																																										
#40	15 – 50	25 – 80	--	--	--	--																																																																																										
#200	0 – 25	10 – 35	3 – 15	0 – 19	3 – 20	0 – 24																																																																																										
	¹⁰ Max 1-in. aggregate when used as a base course under Item P-501, PCC pavement.																																																																																															
	Gradation plots comparing FAA to state agency gradation requirements: <p>The graph plots Percent Passing (Y-axis, 0 to 100) against Sieve Size (X-axis, #200 to 2.5). Three data series are shown: P-304, Gradation A (blue circles), P-304, Gradation B (blue squares), and CALTRANS, Class A (orange triangles). The P-304 curves are steeper than the CALTRANS curve, indicating more uniform gradation.</p> <table border="1"> <caption>Data points estimated from the gradation plot</caption> <thead> <tr> <th>Sieve Size</th> <th>P-304, Gradation A (%)</th> <th>P-304, Gradation B (%)</th> <th>CALTRANS, Class A (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#40</td> <td>50</td> <td>25</td> <td>15</td> </tr> <tr> <td>#30</td> <td>80</td> <td>45</td> <td>40</td> </tr> <tr> <td>#10</td> <td>100</td> <td>80</td> <td>60</td> </tr> <tr> <td>#4</td> <td>100</td> <td>55</td> <td>40</td> </tr> <tr> <td>0.75</td> <td>90</td> <td>70</td> <td>70</td> </tr> <tr> <td>1.0</td> <td>100</td> <td>100</td> <td>100</td> </tr> <tr> <td>2.0</td> <td>100</td> <td>100</td> <td>100</td> </tr> </tbody> </table>							Sieve Size	P-304, Gradation A (%)	P-304, Gradation B (%)	CALTRANS, Class A (%)	#200	0	0	0	#40	50	25	15	#30	80	45	40	#10	100	80	60	#4	100	55	40	0.75	90	70	70	1.0	100	100	100	2.0	100	100	100																																																					
Sieve Size	P-304, Gradation A (%)	P-304, Gradation B (%)	CALTRANS, Class A (%)																																																																																													
#200	0	0	0																																																																																													
#40	50	25	15																																																																																													
#30	80	45	40																																																																																													
#10	100	80	60																																																																																													
#4	100	55	40																																																																																													
0.75	90	70	70																																																																																													
1.0	100	100	100																																																																																													
2.0	100	100	100																																																																																													

Item	CEMENT-TREATED BASE COURSE																																				
	FAA and Caltrans Aggregate Gradation Requirements																																				
Additional Specifications (Continued)	<p style="text-align: center;">P-304 Cement Treated Base Course</p>  <p>The graph plots Percent Passing (Y-axis, 0 to 100) against Sieve Size (X-axis, showing #200, #40, #30, #10, #4, 0.75, 1.0, 2.0, 3.0 mm). Three curves are shown: P-304, Gradation A (blue circles), P-304, Gradation B (blue squares), and CALTRANS, Class B (orange triangles). All curves show a sharp increase in passing percentage as the sieve size increases, with Gradation B having the steepest slope.</p> <table border="1"> <thead> <tr> <th>Sieve Size (mm)</th> <th>P-304, Gradation A (%)</th> <th>P-304, Gradation B (%)</th> <th>CALTRANS, Class B (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>2</td> <td>10</td> <td>5</td> </tr> <tr> <td>#40</td> <td>50</td> <td>25</td> <td>15</td> </tr> <tr> <td>#10</td> <td>80</td> <td>45</td> <td>35</td> </tr> <tr> <td>#4</td> <td>100</td> <td>55</td> <td>70</td> </tr> <tr> <td>0.75</td> <td></td> <td></td> <td>85</td> </tr> <tr> <td>1.0</td> <td></td> <td></td> <td>90</td> </tr> <tr> <td>2.0</td> <td></td> <td></td> <td>100</td> </tr> <tr> <td>3.0</td> <td></td> <td></td> <td>100</td> </tr> </tbody> </table>	Sieve Size (mm)	P-304, Gradation A (%)	P-304, Gradation B (%)	CALTRANS, Class B (%)	#200	2	10	5	#40	50	25	15	#10	80	45	35	#4	100	55	70	0.75			85	1.0			90	2.0			100	3.0			100
Sieve Size (mm)	P-304, Gradation A (%)	P-304, Gradation B (%)	CALTRANS, Class B (%)																																		
#200	2	10	5																																		
#40	50	25	15																																		
#10	80	45	35																																		
#4	100	55	70																																		
0.75			85																																		
1.0			90																																		
2.0			100																																		
3.0			100																																		

Item	ECONOCRETE BASE COURSE	
	Caltrans	FAA
Agency Specification	Section 28, Lean Concrete Base	Item P-306, Econcrete Base Course (Lean Mix Concrete Base Course)
Description	This work shall consist of constructing a lean concrete base consisting of a mixture of aggregate, portland cement, water, and at the option of the contractor, water reducing and air-entraining chemical admixtures.	Subbase material composed of uniformly mixed aggregate, cement, and water. May also include approved cementitious additives (fly ash or slag) and chemical admixtures.
Test Methods Referenced	<ul style="list-style-type: none"> ▪ ASTM C150 ▪ California Test 548 	<ul style="list-style-type: none"> ▪ ASTM C150 or ASTM C595 ▪ ASTM C618 ▪ ASTM C989
Materials	<ul style="list-style-type: none"> ▪ Portland cement (Type II Modified) ▪ Aggregate ▪ Water 	<ul style="list-style-type: none"> ▪ Aggregate ▪ Cement, pozzolan, ground granulated blast furnace slag ▪ Chemical admixtures ▪ Water
Relevant Material Requirement(s)	<p>Aggregate:</p> <ul style="list-style-type: none"> ▪ Aggregate shall be of such quality that when mixed with ≤ 300 lb/yd³ Type II modified portland cement, the compressive strength is ≥ 700 psi at 7 days, determined according to California Test 548. ▪ Quality requirements: <ul style="list-style-type: none"> – Sand Equivalent <ul style="list-style-type: none"> ▪ Operating range: ≥ 21 ▪ Contract compliance: ≥ 18 – Clean and free from vegetation and other deleterious substances. <p>Portland cement:</p> <ul style="list-style-type: none"> ▪ Type II modified portland cement meeting ASTM C150 and the following: <ul style="list-style-type: none"> – Equivalent alkalis, max content: 0.60% – Autoclave expansion: $\leq 0.50\%$ – Mortar, containing the cement to be used and Ottawa silica sand, when tested according to California Test 527, shall not expand in water $> 0.010\%$ and shall not contract in air $> 0.048\%$. 	<p>Portland cement:</p> <ul style="list-style-type: none"> ▪ Type I, II, III, IV, or V portland cement meeting ASTM C150. ▪ Type IS, IS-A, IP, IP-A, P, or PA blended cement meeting ASTM C595. <p>Pozzolan materials:</p> <ul style="list-style-type: none"> ▪ Class F fly ash meeting ASTM C618 <p>Ground granulated blast furnace slag:</p> <ul style="list-style-type: none"> ▪ Grade 80, 100, or 120 meeting ASTM C989.
Important Deviations	None	
Level of Acceptability for Use	<ul style="list-style-type: none"> ▪ Group 2 – The state-specified material does not meet the FAA gradation requirements. The state-specified material may be used on airfields supporting aircraft with less than 60,000 lbs maximum takeoff weight. ▪ Group 3 – The state-specified material may be used on FAA facilities if the requirements for aggregate gradation are met. 	

Item	ECONOCRETE BASE COURSE																																																																																									
	FAA and Caltrans Aggregate Gradation Requirements																																																																																									
Additional Specifications	Gradation requirements:																																																																																									
		<table border="1"> <thead> <tr> <th rowspan="3">Sieve</th> <th colspan="6">% Passing</th> </tr> <tr> <th colspan="2">FAA</th> <th colspan="4">CALTRANS</th> </tr> <tr> <th>1 1/2-in. max</th> <th>1-in. max</th> <th>Operating Range</th> <th>Contract Compliance</th> <th>Operating Range</th> <th>Contract Compliance</th> </tr> </thead> <tbody> <tr> <td>2 in.</td> <td>--</td> <td>--</td> <td>100</td> <td>100</td> <td>--</td> <td>--</td> </tr> <tr> <td>1-1/2 in.</td> <td>100</td> <td>--</td> <td>90 – 100</td> <td>87 – 100</td> <td>100</td> <td>100</td> </tr> <tr> <td>1 in.</td> <td>70 – 95</td> <td>100</td> <td>--</td> <td>--</td> <td>90 – 100</td> <td>87 – 100</td> </tr> <tr> <td>3/4 in.</td> <td>55 – 85</td> <td>70 – 100</td> <td>50 – 85</td> <td>45 – 90</td> <td>50 – 100</td> <td>45 – 100</td> </tr> <tr> <td>3/8 in.</td> <td>--</td> <td>--</td> <td>40 – 75</td> <td>35 – 80</td> <td>40 – 75</td> <td>35 – 80</td> </tr> <tr> <td>#4</td> <td>30 – 60</td> <td>35 – 65</td> <td>25 – 60</td> <td>20 – 65</td> <td>35 – 60</td> <td>30 – 65</td> </tr> <tr> <td>#30</td> <td>--</td> <td>--</td> <td>10 – 30</td> <td>6 – 34</td> <td>10 – 30</td> <td>6 – 34</td> </tr> <tr> <td>#40</td> <td>10 – 30</td> <td>15 – 30</td> <td>--</td> <td>--</td> <td>--</td> <td>--</td> </tr> <tr> <td>#200</td> <td>0 – 15</td> <td>0 – 15</td> <td>0 – 12</td> <td>0 – 15</td> <td>0 – 12</td> <td>0 – 15</td> </tr> </tbody> </table>							Sieve	% Passing						FAA		CALTRANS				1 1/2-in. max	1-in. max	Operating Range	Contract Compliance	Operating Range	Contract Compliance	2 in.	--	--	100	100	--	--	1-1/2 in.	100	--	90 – 100	87 – 100	100	100	1 in.	70 – 95	100	--	--	90 – 100	87 – 100	3/4 in.	55 – 85	70 – 100	50 – 85	45 – 90	50 – 100	45 – 100	3/8 in.	--	--	40 – 75	35 – 80	40 – 75	35 – 80	#4	30 – 60	35 – 65	25 – 60	20 – 65	35 – 60	30 – 65	#30	--	--	10 – 30	6 – 34	10 – 30	6 – 34	#40	10 – 30	15 – 30	--	--	--	--	#200	0 – 15	0 – 15	0 – 12	0 – 15	0 – 12	0 – 15
Sieve	% Passing																																																																																									
	FAA		CALTRANS																																																																																							
	1 1/2-in. max	1-in. max	Operating Range	Contract Compliance	Operating Range	Contract Compliance																																																																																				
2 in.	--	--	100	100	--	--																																																																																				
1-1/2 in.	100	--	90 – 100	87 – 100	100	100																																																																																				
1 in.	70 – 95	100	--	--	90 – 100	87 – 100																																																																																				
3/4 in.	55 – 85	70 – 100	50 – 85	45 – 90	50 – 100	45 – 100																																																																																				
3/8 in.	--	--	40 – 75	35 – 80	40 – 75	35 – 80																																																																																				
#4	30 – 60	35 – 65	25 – 60	20 – 65	35 – 60	30 – 65																																																																																				
#30	--	--	10 – 30	6 – 34	10 – 30	6 – 34																																																																																				
#40	10 – 30	15 – 30	--	--	--	--																																																																																				
#200	0 – 15	0 – 15	0 – 12	0 – 15	0 – 12	0 – 15																																																																																				
		Gradation plots comparing FAA to state agency gradation requirements:																																																																																								
		 <p>P-306 Econoconcrete Base Course</p> <p>Percent Passing</p> <p>Sieve Size</p> <p>Legend:</p> <ul style="list-style-type: none"> P-306, 1 in. (Blue solid line with circles) P-306, 1 1/2 in. (Blue dashed line with squares) CALTRANS, 1 in. max (Orange solid line with triangles) <table border="1"> <caption>Approximate data points from the gradation plot</caption> <thead> <tr> <th>Sieve Size</th> <th>P-306, 1 in. (%)</th> <th>P-306, 1 1/2 in. (%)</th> <th>CALTRANS, 1 in. max (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#40</td> <td>15</td> <td>10</td> <td>30</td> </tr> <tr> <td>#30</td> <td>18</td> <td>12</td> <td>30</td> </tr> <tr> <td>#4</td> <td>65</td> <td>30</td> <td>60</td> </tr> <tr> <td>0.375</td> <td>70</td> <td>55</td> <td>75</td> </tr> <tr> <td>0.75</td> <td>95</td> <td>85</td> <td>90</td> </tr> <tr> <td>1.0</td> <td>100</td> <td>100</td> <td>100</td> </tr> </tbody> </table>							Sieve Size	P-306, 1 in. (%)	P-306, 1 1/2 in. (%)	CALTRANS, 1 in. max (%)	#200	0	0	0	#40	15	10	30	#30	18	12	30	#4	65	30	60	0.375	70	55	75	0.75	95	85	90	1.0	100	100	100																																																		
Sieve Size	P-306, 1 in. (%)	P-306, 1 1/2 in. (%)	CALTRANS, 1 in. max (%)																																																																																							
#200	0	0	0																																																																																							
#40	15	10	30																																																																																							
#30	18	12	30																																																																																							
#4	65	30	60																																																																																							
0.375	70	55	75																																																																																							
0.75	95	85	90																																																																																							
1.0	100	100	100																																																																																							

Item	ECONOCRETE BASE COURSE																																				
	FAA and Caltrans Aggregate Gradation Requirements																																				
Additional Specifications (Continued)	<p>P-306 Econoconcrete Base Course</p> <table border="1"> <caption>Approximate Gradation Data for P-306 Econoconcrete Base Course</caption> <thead> <tr> <th>Sieve Size</th> <th>P-306, 1 in. (%)</th> <th>P-306, 1 1/2 in. (%)</th> <th>CALTRANS, 1 1/2 in. max (%)</th> </tr> </thead> <tbody> <tr> <td>#200</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>#40</td> <td>15</td> <td>10</td> <td>10</td> </tr> <tr> <td>#30</td> <td>15</td> <td>10</td> <td>10</td> </tr> <tr> <td>#4</td> <td>65</td> <td>30</td> <td>25</td> </tr> <tr> <td>0.375</td> <td>98</td> <td>55</td> <td>50</td> </tr> <tr> <td>0.75</td> <td>100</td> <td>70</td> <td>75</td> </tr> <tr> <td>1.0</td> <td>100</td> <td>95</td> <td>90</td> </tr> <tr> <td>2.0</td> <td>100</td> <td>100</td> <td>100</td> </tr> </tbody> </table>	Sieve Size	P-306, 1 in. (%)	P-306, 1 1/2 in. (%)	CALTRANS, 1 1/2 in. max (%)	#200	0	0	0	#40	15	10	10	#30	15	10	10	#4	65	30	25	0.375	98	55	50	0.75	100	70	75	1.0	100	95	90	2.0	100	100	100
Sieve Size	P-306, 1 in. (%)	P-306, 1 1/2 in. (%)	CALTRANS, 1 1/2 in. max (%)																																		
#200	0	0	0																																		
#40	15	10	10																																		
#30	15	10	10																																		
#4	65	30	25																																		
0.375	98	55	50																																		
0.75	100	70	75																																		
1.0	100	95	90																																		
2.0	100	100	100																																		

Item	PORTLAND CEMENT CONCRETE PAVEMENT	
	Caltrans	FAA
Agency Specification	Section 40, Portland Cement Concrete Pavement	Item P-501, Portland Cement Concrete Pavement
Description	This work shall consist of constructing a pavement of portland cement concrete on a prepared subgrade, with or without forms.	Pavement course composed of portland cement concrete, with or without reinforcement.
Test Methods Referenced	<ul style="list-style-type: none"> ▪ ASTM C114 ▪ ASTM C150 ▪ ASTM C311 ▪ ASTM C595 ▪ ASTM C618 ▪ ASTM C1240 ▪ ASTM D4326 ▪ California Test 211 ▪ California Test 213 ▪ California Test 214 ▪ California Test 217 ▪ California Test 229 ▪ California Test 515 ▪ California Test 527 	<ul style="list-style-type: none"> ▪ ASTM C33 ▪ ASTM C131 ▪ ASTM C150 or ASTM C595 or ASTM C1157 ▪ ASTM C618
Materials	<ul style="list-style-type: none"> ▪ Portland cement concrete (Class 3) <ul style="list-style-type: none"> – Cement (Type II Modified, Type IP (MS) Modified, and Type V) – Water – Coarse aggregate – Fine aggregate – Admixture materials <ul style="list-style-type: none"> ▪ Chemical admixtures ▪ Air-entraining admixtures ▪ Calcium chloride ▪ Mineral admixtures 	<ul style="list-style-type: none"> ▪ Fine and coarse aggregate ▪ Cement, fly ash, natural pozzolan, or ground blast furnace slag ▪ Water ▪ Cover material for curing ▪ Admixtures
Relevant Material Requirement(s)	<p>Coarse aggregate:</p> <ul style="list-style-type: none"> ▪ Crushed or uncrushed gravel, crushed stone, crushed air-cooled iron blast furnace slag¹¹, or a combination of these. ▪ Natural aggregates shall be thoroughly and uniformly washed before use. ▪ Quality requirements: <ul style="list-style-type: none"> – Soundness (California Test 214), max loss: 10% – Wear (California Test 211), max loss: 45% – Cleanliness Value (California Test 211): <ul style="list-style-type: none"> ▪ Operating range: ≥ 75 ▪ Contract compliance: ≥ 71 – Free from deleterious coatings, clay balls, roots, bark, sticks, rags, and other extraneous material. <p>¹¹ Crushed air-cooled blast furnace slag shall not be used in reinforced concrete.</p>	<p>Coarse aggregate:</p> <ul style="list-style-type: none"> ▪ Crushed or uncrushed gravel, crushed stone, air-cooled blast furnace slag, or crushed recycled PCC. ▪ Coarse aggregate shall meet ASTM C33. ▪ Quality requirements: <ul style="list-style-type: none"> – Wear (ASTM C131), max loss <ul style="list-style-type: none"> ▪ Used as surface course, 40% ▪ Used as base course, 50% <p>Fine aggregate:</p> <ul style="list-style-type: none"> ▪ Fine aggregate shall meet ASTM C33. <p>Portland cement:</p> <ul style="list-style-type: none"> ▪ Type I, II, III, or V meeting ASTM C150 ▪ Type IS or IP meeting ASTM C595 ▪ Type GU, HE, HS, MH, or LH meeting ASTM C1157

Item	PORTLAND CEMENT CONCRETE PAVEMENT	
	Caltrans	FAA
	<p>Fine aggregate:</p> <ul style="list-style-type: none"> Natural aggregates shall be thoroughly and uniformly washed before use. Quality requirements: <ul style="list-style-type: none"> Soundness (California Test 214), max loss¹²: 10% Sand Equivalent (California Test 217): <ul style="list-style-type: none"> Operating range: ≥ 75 Contract compliance: ≥ 71 Organic Impurities (California Test 213): "satisfactory"¹³ Relative mortar strengths (California Test 515): $\geq 95\%$ Free from deleterious coatings, clay balls, roots, bark, sticks, rags, and other extraneous material. <p>¹² Will be waived provided the durability index (Df) is ≥ 60, determined according to California Test 229.</p> <p>¹³ Fine aggregate developing a color darker than the reference solution may be accepted based on mortar strength tests.</p> <p>Portland cement:</p> <ul style="list-style-type: none"> Type II Modified portland cement meeting ASTM C150, and Type IP (MS) Modified blended cement meeting ASTM C595. Additionally, both shall meet the following: <ul style="list-style-type: none"> Equivalent alkalis, max content: 0.60% Autoclave expansion: $\leq 0.50\%$ Mortar, containing the cement to be used and Ottawa silica sand, when tested according to California Test 527, shall not expand in water $> 0.010\%$ and shall not contract in air $> 0.048\%$. Type V portland cement meeting ASTM C150 and the following: <ul style="list-style-type: none"> Equivalent alkalis, max content: 0.60% Autoclave expansion: $\leq 0.50\%$ Mortar, containing the cement to be used and Ottawa silica sand, when tested according to California Test 527, shall not expand in water $> 0.010\%$ and shall not contract in air $> 0.075\%$. Type IP (MS) Modified blended cement shall be a uniform blend of Type II portland cement and $\leq 35\%$ mineral admixture, by weight, meeting the following: <ul style="list-style-type: none"> Coal fly ash Raw or calcined natural pozzolan meeting ASTM C618 Silica fume meeting ASTM C1240 and with reduction of mortar expansion $\geq 80\%$ Chemical requirements for all mineral admixtures: <ul style="list-style-type: none"> Calcium oxide content (ASTM C114): $\leq 10\%$ Available alkali content (ASTM C311): $\leq 1.5\%$, or Total alkali content (ASTM 	

Item	PORTLAND CEMENT CONCRETE PAVEMENT	
	Caltrans	FAA
	D4326): $\leq 5.0\%$	
Important Deviations	None	
Contractor Notes		The contractor may choose to purchase individual aggregates based upon ASTM C33 or SHA gradations. However, it is advisable to specify the standard size or name, gradation, and sieve tolerances. Use of ASTM C33 or SHA materials does not negate meeting the aggregate quality requirements.
Level of Acceptability for Use	<ul style="list-style-type: none"> ▪ Group 2 – The state-specified material does not meet the FAA requirements for ASTM C131 or aggregate gradation. The state-specified material (excluding Caltrans 1/2 in x No. 4 and 3/8 in x No. 8 gradations) may be used on airfields supporting aircraft with less than 60,000 lbs maximum takeoff weight. ▪ Group 3¹⁴ – The state-specified material may be used on FAA facilities if the requirements for ASTM C131 (of the surface course) and aggregate gradation are met. <p>Note – All state materials must comply with FAA Engineering Brief 70 when pavement deicing chemicals are used.</p>	

¹⁴ Note that FAA Item P-501 states:

The Engineer shall specify the aggregate to be furnished from the table shown in this note. The appropriate gradation shall be inserted into Table 2. Insert points are denoted by asterisks. Where locally available aggregates cannot be economically blended to meet the grading requirements, the gradations may be modified by the Engineer to fit the characteristics of such locally available aggregates.

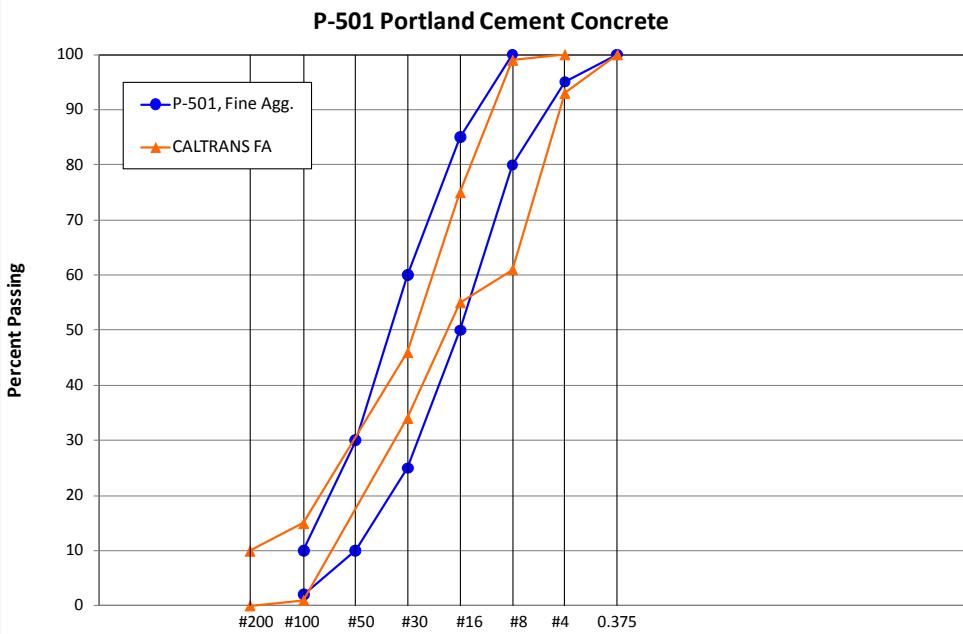
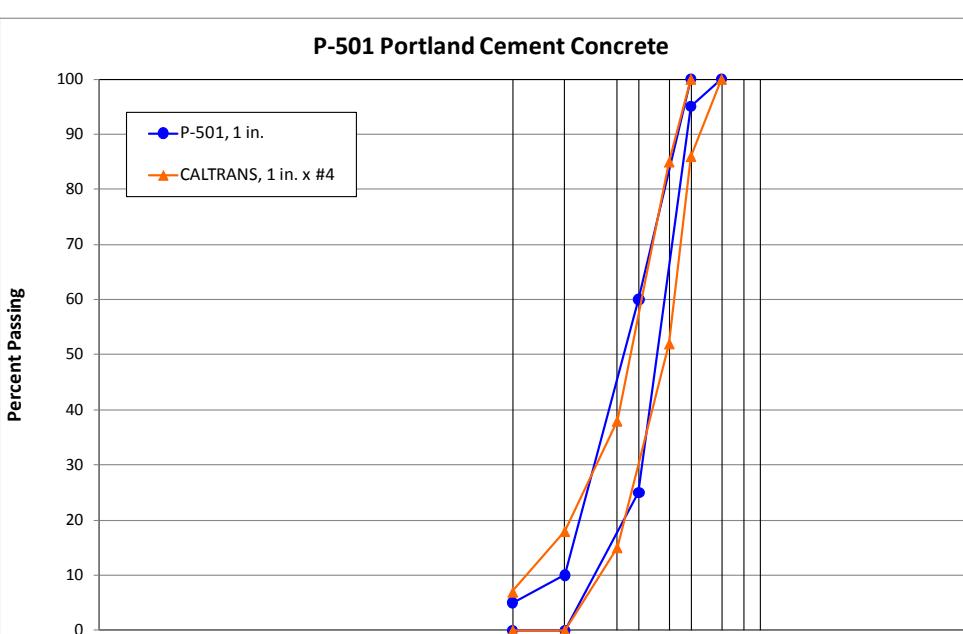
This indicates the engineer can choose to accept the local gradation, in this case changing the category from a Group 3 to a Group 1. It is noted that he/she would still need to file a “modification to standard” request to the FAA to obtain material approval.

Similarly, the FAA Item P-501 also states:

The Engineer shall specify the percentage of wear. It should not exceed 40 percent. In certain cases where aggregate of this quality cannot be obtained economically, aggregate with a higher percentage of wear may be used if a satisfactory service record of at least 5 years' duration under similar conditions of service and exposure has been demonstrated.

Again, this provides a mechanism for the engineer to accept aggregate with a higher percentage of wear, but with the stipulation that a “modification to standard” request would need to be filed with the FAA to obtain material approval.

Item	PORTLAND CEMENT CONCRETE PAVEMENT							
	FAA and Caltrans Aggregate Gradation Requirements							
Additional Specifications	Gradation requirements: Modified gradations fitting characteristics of local aggregates or producing concrete mixes with well-graded or optimized aggregate combinations may be permitted with FAA approval.							
COARSE AGGREGATE								
Sieve	% Passing				CALTRANS			
	FAA	2 in. max¹⁵	1-1/2 in. max¹⁵	1 in. max	3/4 in. max	1-1/2 in. x 3/4 in.	1 in. x #4	1/2 in. x #4
2-1/2 in.	100	--	--	--	--	--	--	--
2 in.	90 – 100	100	--	--	100	--	--	--
1-1/2 in.	35 – 70	90 – 100	100	--	85 – 100	100	--	--
1 in.	0 – 15	20 – 55	95 – 100	100	19 – 41	86 – 100	--	--
3/4 in.	--	0 – 15	--	90 – 100	0 – 20	52 – 85	100	--
1/2 in.	0 – 5	--	25 – 60	--	--	--	80 – 100	100
3/8 in.	--	0 – 5	--	20 – 55	0 – 9	15 – 38	40 – 78	50 – 85
#4	--	--	0 – 10	0 – 10	--	0 – 18	0 – 18	0 – 28
#8	--	--	0 – 5	0 – 5	--	0 – 7	0 – 7	0 – 7
¹⁵ Aggregate shall be furnished in two size groups when the nominal max size is greater than 1 in.								
Fine Aggregate								
Sieve	% Passing							
	FAA	CALTRANS						
3/8 in.	100	100						
#4	95 – 100	93 – 100						
#8	80 – 100	61 – 99						
#16	50 – 85	55 – 75 ¹⁶						
#30	25 – 60	34 – 46 ¹⁶						
#50	10 – 30	16 – 29 ¹⁶						
#100	2 – 10	1 – 15						
#200	--	0 – 10						
¹⁶ Distribution of fine aggregate sizes shall be such that the difference between the percents passing the #16 and #30 sieves and the percents passing the #30 and #50 sieves shall be between 10 and 40.								

Item	PORTLAND CEMENT CONCRETE PAVEMENT																																																			
	FAA and Caltrans Aggregate Gradation Requirements																																																			
Additional Specifications (Continued)	<p>Gradation plots comparing FAA to state agency gradation requirements:</p> <div style="display: flex; justify-content: space-around;"> <div style="text-align: center;"> <p>P-501 Portland Cement Concrete</p>  <table border="1"> <caption>Data for P-501 Portland Cement Concrete Gradation Plot</caption> <thead> <tr> <th>Sieve Size</th> <th>P-501, Fine Agg. (%)</th> <th>CALTRANS FA (%)</th> </tr> </thead> <tbody> <tr><td>#200</td><td>0</td><td>0</td></tr> <tr><td>#100</td><td>10</td><td>15</td></tr> <tr><td>#50</td><td>30</td><td>10</td></tr> <tr><td>#30</td><td>60</td><td>45</td></tr> <tr><td>#16</td><td>85</td><td>55</td></tr> <tr><td>#8</td><td>80</td><td>60</td></tr> <tr><td>#4</td><td>100</td><td>100</td></tr> <tr><td>0.375</td><td>100</td><td>100</td></tr> </tbody> </table> </div> <div style="text-align: center;"> <p>P-501 Portland Cement Concrete</p>  <table border="1"> <caption>Data for P-501 Portland Cement Concrete Gradation Plot (1 in. sizes)</caption> <thead> <tr> <th>Sieve Size</th> <th>P-501, 1 in. (%)</th> <th>CALTRANS, 1 in. x #4 (%)</th> </tr> </thead> <tbody> <tr><td>#8</td><td>5</td><td>5</td></tr> <tr><td>#4</td><td>10</td><td>20</td></tr> <tr><td>0.375</td><td>60</td><td>38</td></tr> <tr><td>0.5</td><td>25</td><td>15</td></tr> <tr><td>0.75</td><td>100</td><td>52</td></tr> <tr><td>1.0</td><td>100</td><td>85</td></tr> <tr><td>1.5</td><td>100</td><td>100</td></tr> </tbody> </table> </div> </div>	Sieve Size	P-501, Fine Agg. (%)	CALTRANS FA (%)	#200	0	0	#100	10	15	#50	30	10	#30	60	45	#16	85	55	#8	80	60	#4	100	100	0.375	100	100	Sieve Size	P-501, 1 in. (%)	CALTRANS, 1 in. x #4 (%)	#8	5	5	#4	10	20	0.375	60	38	0.5	25	15	0.75	100	52	1.0	100	85	1.5	100	100
Sieve Size	P-501, Fine Agg. (%)	CALTRANS FA (%)																																																		
#200	0	0																																																		
#100	10	15																																																		
#50	30	10																																																		
#30	60	45																																																		
#16	85	55																																																		
#8	80	60																																																		
#4	100	100																																																		
0.375	100	100																																																		
Sieve Size	P-501, 1 in. (%)	CALTRANS, 1 in. x #4 (%)																																																		
#8	5	5																																																		
#4	10	20																																																		
0.375	60	38																																																		
0.5	25	15																																																		
0.75	100	52																																																		
1.0	100	85																																																		
1.5	100	100																																																		

Item	PORTLAND CEMENT CONCRETE PAVEMENT																									
	FAA and Caltrans Aggregate Gradation Requirements																									
Additional Specifications (Continued)		<p>P-501 Portland Cement Concrete</p> <table border="1"><caption>Approximate data points from the gradation curve graph</caption><thead><tr><th>Sieve Size</th><th>P-501, 1 1/2 in. (%)</th><th>CALTRANS, 1-1/2 in. x 3/4 in. (%)</th></tr></thead><tbody><tr><td>0.375</td><td>0</td><td>0</td></tr><tr><td>0.5</td><td>0</td><td>0</td></tr><tr><td>0.75</td><td>15</td><td>10</td></tr><tr><td>1.0</td><td>15</td><td>10</td></tr><tr><td>1.25</td><td>55</td><td>40</td></tr><tr><td>1.5</td><td>90</td><td>100</td></tr><tr><td>2.0</td><td>0</td><td>0</td></tr></tbody></table>	Sieve Size	P-501, 1 1/2 in. (%)	CALTRANS, 1-1/2 in. x 3/4 in. (%)	0.375	0	0	0.5	0	0	0.75	15	10	1.0	15	10	1.25	55	40	1.5	90	100	2.0	0	0
Sieve Size	P-501, 1 1/2 in. (%)	CALTRANS, 1-1/2 in. x 3/4 in. (%)																								
0.375	0	0																								
0.5	0	0																								
0.75	15	10																								
1.0	15	10																								
1.25	55	40																								
1.5	90	100																								
2.0	0	0																								